



Politecnico
di Bari

Repository Istituzionale dei Prodotti della Ricerca del Politecnico di Bari

Epindolidiones-Versatile and Stable Hydrogen-Bonded Pigments for Organic Field-Effect Transistors and Light-Emitting Diodes

This is a pre-print of the following article

Original Citation:

Epindolidiones-Versatile and Stable Hydrogen-Bonded Pigments for Organic Field-Effect Transistors and Light-Emitting Diodes / Gowacki, E. D.; Romanazzi, Giuseppe; Yumusak, C.; Coskun, H.; Monkowius, U.; Voss, G.; Burian, M.; Lechner, R. T.; Demitri, N.; Redhammer, G. J.; Sünger, N.; Suranna, Gian Paolo; Sariciftci, S.. - In: ADVANCED FUNCTIONAL MATERIALS. - ISSN 1616-301X. - STAMPA. - 25:5(2015), pp. 776-787. [10.1002/adfm.201402539]

Availability:

This version is available at <http://hdl.handle.net/11589/3273> since: 2021-03-04

Published version

DOI:10.1002/adfm.201402539

Publisher:

Terms of use:

(Article begins on next page)

Advanced Functional Materials

Epindolidiones - versatile and stable hydrogen-bonded pigments for organic field-effect transistors and light-emitting diodes --Manuscript Draft--

Manuscript Number:	
Full Title:	Epindolidiones - versatile and stable hydrogen-bonded pigments for organic field-effect transistors and light-emitting diodes
Article Type:	Full Paper
Section/Category:	
Keywords:	hydrogen-bonded organic semiconductors; organic pigments; indigoids; organic field-effect transistors; organic electronics
Corresponding Author:	Eric Daniel Glowacki Johannes Kepler University AUSTRIA
Additional Information:	
Question	Response
<p>Please submit a plain text version of your cover letter here.</p> <p>If you are submitting a revision of your manuscript, please do not overwrite your original cover letter. There is an opportunity for you to provide your responses to the reviewers later; please do not add them here.</p>	<p>To the Advanced Functional Materials editorial staff,</p> <p>Please find enclosed our original submission entitled "Epindolidiones – versatile and stable hydrogen-bonded pigments for organic field-effect transistors and light-emitting diodes" to be considered for publication in Advanced Functional Materials.</p> <p>In this work we explore the semiconducting properties of epindolidiones, a highly-stable organic hydrogen-bonded pigment family. The class of materials known as H-bonded pigments has not been explored until very recently in the field of organic electronics as they are perceived as having inferior π-conjugation – they were simply not expected to work as semiconductors. Nevertheless, such materials are in ubiquitous use industrially, renowned for stability, non-toxicity, and low cost. In this paper we explore electronic transport in three epindolidiones, correlating it with their crystal structure which we have been successful in measuring, and their optical properties. We evaluate the extraordinary operational stability of field-effect transistor devices, which can operate stably in various ionic solutions in a pH range from 3-10 without any passivation. We discuss in detail also epindolidione synthesis, as well as preparation and properties of latent pigment derivatives which allow solution processing. We think this work will stimulate more exploration into using low-cost industrial pigments as viable electronic materials. Additionally, the impressive stability in aqueous ionic environments is of substantial interest for the growing field of deploying organic semiconductors in biochemical applications.</p> <p>We thank you, the editorial team, and referees in advance for consideration of our work.</p>
Corresponding Author Secondary Information:	
Corresponding Author's Institution:	Johannes Kepler University
Corresponding Author's Secondary Institution:	
First Author:	Eric Daniel Glowacki
First Author Secondary Information:	
Order of Authors:	Eric Daniel Glowacki
	Giuseppe Romanazzi
	Cigdem Yumusak
	Halime Coskun

	Uwe Monkowius
	Gundula Voss
	Max Burian
	Rainer Lechner
	Nicola Demetri
	Günther Redhammer
	Nevsal Sunger
	Gian Paolo Suranna
	Serdar Sariciftci
Order of Authors Secondary Information:	
Abstract:	<p>Hydrogen-bonded pigments are remarkably stable organic solids with high-crystal lattice energy. Here we report on a lesser-known family of compounds, the epindolidiones, which we have found demonstrate electronic transport with extraordinary stability, even in highly-demanding aqueous environments. Hole mobilities in the range 0.05 - 1 cm²/Vs can be achieved, with lower electron mobilities of up to 0.1 cm²/Vs. To help understand charge transport in epindolidiones, X-ray diffraction was used to solve the crystal structure of 2,8-difluoroepindolidione and 2,8-dichloroepindolidione. Both derivatives crystallize with a linear-chain H-bonding lattice featuring two-dimensional π-π stacking. Powder diffraction indicates that the unsubstituted epindolidione has very similar crystallinity. All types of epindolidiones measured here display strong low-energy optical emission originating from excimeric states, which coexists with higher-energy fluorescence. This can be exploited in light-emitting diodes, which show the same hybrid singlet and low-energy excimer electroluminescence. We fabricated low-voltage FETs with epindolidione which operate reliably under repeated cyclic tests in ionic solutions within the pH range 3-10 without degradation. Finally, in order to overcome the insolubility of epindolidiones in organic solvents, we devised a procedure to allow solution-processing via the introduction of suitable thermolabile solubilizing groups. This work shows the versatile potential of epindolidione pigments for electronics applications.</p>

DOI: 10.1002/ ((please add manuscript number))

Full Paper

Epindolidiones – versatile and stable hydrogen-bonded pigments for organic field-effect transistors and light-emitting diodes

E. D. Głowacki, G. Romanazzi, C. Yumusak, H. Coskun, U. Monkowius, G. Voss, M. Burian, R. T. Lechner, N. Demetri, G. J. Redhammer, N. Sünger, G. P. Suranna, N. S. Sariciftci*

[*] Dr. E.D. Głowacki, Dr. C. Yumusak, H. Coskun, Dr. G. Voss, Prof. N.S. Sariciftci

Linz Institute for Organic Solar Cells (LIOS)

Johannes Kepler University, A-4040 Linz Austria

E-mail: eric_daniel.glowacki@jku.at

Dr. G. Romanazzi, Prof. G. P. Suranna

Dipartimento di Ingegneria Civile, Ambientale, del Territorio, Edile e di Chimica (DICATECh), Politecnico di Bari, Via Orabona 4, 70125, Bari, Italy

Dr. C. Yumusak

Department of Physics, Faculty of Arts and Sciences, Yildiz Technical University, Davutpasa Campus, Esenler, 34210 Istanbul, Turkey

Prof. U. Monkowius

Institute of Inorganic Chemistry

Johannes Kepler University, A-4040 Linz Austria

M. Burian, Prof. R. T. Lechner

Institute of Physics, Montanuniversitaet Leoben, Franz-Josef-Strasse

18, 8700 Leoben, Austria

N. Demetri

Elettra – Sincrotrone Trieste, S.S. 14 Km 163.5 in Area Science Park,

34149 Basovizza, Trieste, Italy

Dr. G. J. Redhammer,

Materialwissenschaften und Physik, Abteilung für Mineralogie, Paris-Lodron Universität

Salzburg, Hellabrunner Str. 34, 5020 Salzburg, Austria

N. Sünger

Solar Energy Institute, Ege University, Izmir, Turkey

Keywords: hydrogen-bonded organic semiconductors, organic pigments, indigoids, organic field-effect transistors, organic electronics

Abstract: Hydrogen-bonded pigments are remarkably stable high-crystal lattice energy organic solids. Here we report on a lesser-known family of compounds, the epindolidiones, which we have found demonstrate electronic transport with extraordinary stability, even in highly-demanding aqueous environments. Hole mobilities in the range $0.05 - 1 \text{ cm}^2/\text{Vs}$ can be achieved, with lower electron mobilities of up to $0.1 \text{ cm}^2/\text{Vs}$. To help understand charge transport in epindolidiones, X-ray diffraction was used to solve the crystal structure of 2,8-difluoroepindolidione and 2,8-dichloroepindolidione. Both derivatives crystallize with a linear-chain H-bonding lattice featuring two-dimensional π - π stacking. Powder diffraction

1 indicates that the unsubstituted epindolidione has very similar crystallinity. All types of
2 epindolidiones measured here display strong low-energy optical emission originating from
3 excimeric states, which coexists with higher-energy fluorescence. This can be exploited in
4 light-emitting diodes, which show the same hybrid singlet and low-energy excimer
5 electroluminescence. We fabricated low-voltage FETs with epindolidione which operate
6 reliably under repeated cyclic tests in different ionic solutions within the pH range 3-10
7 without degradation. Finally, in order to overcome the insolubility of epindolidiones in
8 organic solvents, we devised a chemical procedure to allow solution-processing via the
9 introduction of suitable thermolabile solubilizing groups. This work shows the versatile
10 potential of epindolidione pigments for electronics applications.
11
12
13
14
15
16
17
18

19 1. Introduction

20 Hydrogen-bonded organic pigments are a class of materials familiar from applications in the
21 colorant industry, where they find widespread use as materials for robust outdoor paints,
22 cosmetics, and printing inks.^[1,2] Indigo, a natural product, is the oldest and still most widely
23 produced organic dye and pigment (**Figure 1**).^[3] The intermolecular $-\text{NH}\cdots\text{O}=\text{C}$ hydrogen
24 bonding that characterizes indigo is exploited in most of the synthetic hydrogen-bonded
25 pigments as well. This class of materials has proven to be nontoxic and safe for humans, and
26 is considered safer than even several classes of food dyes.^[4] Recently, we have found that
27 indigo^[5] and some of its derivatives^[6,7] demonstrate ambipolar transport in organic field-effect
28 transistors (OFETs), with mobility ranging from 0.01 – 0.4 cm^2/Vs . We then reported on
29 quinacridone, a common industrial colorant perhaps best known as constituting the magenta
30 printer pigment, as an ambipolar semiconductor with mobility in the 0.01-0.1 cm^2/Vs range
31 (Figure 1).^[8] Quinacridone also demonstrated the formation of low-energy luminescent
32 species, attributed to charge transfer excitons, which led to a low effective exciton binding
33 energy and promising photovoltaic behavior.^[9] Alongside quinacridone, we evaluated its 4-
34 ring analog epindolidione (Figure 1). Epindolidione demonstrated promising behavior in
35 OFETs, providing hole mobility as high as 1.5 cm^2/Vs with excellent stability in air.^[8] Indigo,
36 epindolidione, and quinacridone are all examples of hydrogen-bonded pigments where
37 interplay between intermolecular H-bonds and π - π stacking interactions lead to strong
38 intermolecular interactions and high crystal lattice energy solids.^[1,2,10] A substantial
39 bathochromic shift in absorption accompanied by increased oscillator strength occurs from
40 dilute solutions to the solid state (Figure 1b). Intramolecular H-bonding in indigo results in
41 ultrafast proton transfer in the excited state, quenching luminescence.^[11] Quinacridone and
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1 epindolidione, in contrast, are highly luminescent in solution. Epindolidione is a structural
2 isomer of indigo, however photophysically it is very different – it is highly luminescent, even
3 in the solid state, and is yellow/orange, instead of blue. Additionally, as we report herein, it
4 crystallizes with a very different structure than indigo. In this work we follow up on the
5 epindolidione class of compounds, detailing synthetic preparation and characterization of
6
7 epindolidiones, their crystalline structure, optical and electrochemical properties, and results
8
9 from OFETs and electroluminescent devices. Finally, we revisit the issue of epindolidione
10
11 OFET stability, showing also that such devices can operate with excellent stability even in
12
13 aqueous environments within a pH range from 3-10.
14
15

16 17 18 2. Results and Discussion 19 20

21 2.1. Synthesis and characterization of epindolidiones 22

23 The synthetic approach followed to obtain the epindolidiones:
24 *dibenzo[b,g][1,5]naphthyridine-6,12(5H,11H)-dione* (Epi), 2,8-
25 *difluorodibenzo[b,g][1,5]naphthyridine-6,12(5H,11H)-dione* (2F-Epi), 2,8-
26 *dichlorodibenzo[b,g][1,5]naphthyridine-6,12(5H,11H)-dione* (2Cl-Epi) is detailed in **Scheme**
27
28 **1** and follows the procedure reported by Jaffe and Matrick,^[12] although the suggestions by
29
30 Kemp *et al.*^[13] concerning the preparation of intermediates 1-3 have also been taken into
31
32 account. Dimethyl dihydroxyfumarate (1) reacts rapidly with aniline, or *p*-fluoroaniline or *p*-
33
34 chloroaniline, under hydrochloric acid catalysis to give precipitation of dimethyl
35
36 bis(arylamino)maleates 2a-c in high yields. The *Z* geometry of 2a-c was confirmed by ¹H-
37
38 NMR spectra as well as by the presence of a very strong FT-IR absorption at 1570 cm⁻¹
39
40 ascribable to the olefinic stretching of maleate. In boiling DowthermTM A and under high
41
42 dilution, maleates 2a-c isomerize into dimethyl bis(arylamino)fumarates, which then undergo
43
44 the expected Conrad-Limpach cyclization to give the corresponding carbomethoxyquinolones
45
46 3a-c in high yields. Eventually, ring closure of 3a-c to give Epi, 2F-Epi, and 2Cl-Epi
47
48 respectively was carried out at 150°C in polyphosphoric acid (PPA) under high dilution
49
50 conditions. After hydrolysis of the PPA solution, epindolidiones Epi, 2F-Epi, 2Cl-Epi
51
52 precipitated as greenish yellow to yellow powders; overall yields with respect to the initial
53
54 amount of dihydroxyfumaric acid were 51.1, 57.8, and 61.1% respectively. The target
55
56 molecules Epi, 2F-Epi, 2Cl-Epi are very sparingly soluble in common organic solvents,
57
58 however, their structures could be confirmed by solution ¹H-NMR in deuterated dimethyl
59
60 sulfoxide (DMSO-*d*₆) or deuteriosulfuric acid (D₂SO₄). Their purity was proven by CHN
61
62
63
64
65

1 elemental analysis. This synthetic procedure can in principle be applied to a wide range of
2 substituted anilines, many of which are well-known commercially-available materials. Thus
3 many epindolidione derivatives can be prepared from cheap aniline building blocks.
4

5 6 7 2.2 Solubilization of epindolidione by *t*-butoxycarbonylation (tBOC protection).

8 The very poor solubility in common organic solvents of Epi limits its thin-film processability
9 to vacuum-evaporation. It also precludes further synthetic chemical derivatization. Thus, the
10 latent pigment approach was pursued in order to obtain a soluble material suitable for
11 solution-processing or further chemical manipulation. Applied to epindolidione, this approach
12 consists of the reaction of the N-H group with di-*tert*-butyl dicarbonate (tBOC)₂O, a well-
13 known protecting group for amine functions. As a result, the H-bond network is transiently
14 disrupted, leading to a solubility improvement of orders of magnitude and thereby allowing
15 solution processing. The tBOC groups are subsequently removed by simple heating (or by
16 acid treatment) with the release of gaseous CO₂ and isobutene. This procedure was introduced
17 for insoluble industrial pigments like diketopyrrolopyrroles and quinacridones by researchers
18 at the *Ciba-Geigy* company.^[14,15]

19 Contrary to other H-bonded pigments, which can readily be functionalized with tBOC
20 according to several simple procedures^[14–16], the *t*-butoxycarbonylation of Epi proved to be
21 quite a demanding task. After several attempts, we were able to find the best protocol
22 (**Scheme 2**) in terms of yields and reaction time. A stoichiometric amount of 4-
23 dimethylaminopyridine (DMAP) and a large excess of (tBOC)₂O were necessary to obtain,
24 after flash chromatography, di-tBOC Epi and mono-tBOC Epi. The persistence of a
25 significant amount of mono-tBOC Epi in the reaction mixture is likely caused by the stability
26 of the *enol* tautomeric form of this compound. ¹H NMR of mono-tBOC Epi in chloroform
27 confirms that the hydroxyquinoline tautomer is dominant in equilibrium in solution,
28 explaining why the reaction with a second tBOC group is impeded.

29 The tBOC derivatives proved to be, as expected, highly soluble: the solubility of di-tBOC Epi
30 reaches concentrations up to ~25 mg/ml in chloroform. Solution processing of films using di-
31 tBOC Epi is described in detail in section 2.7.
32
33

34 35 2.3 Crystal structure

36 An important step in understanding the charge transport in H-bonded epindolidione pigments
37 is to evaluate the solid state structure of such materials. Diffraction-quality single crystals of
38 hydrogen-bonded pigments can typically be grown using physical vapor transport
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

recrystallization. Establishing the crystal structure of the closely-related quinacridone family of pigments presented a challenge to crystallographers for many years, as growing defect-free crystals of suitable size required considerable trial-and-error optimization. Details concerning this long-term effort were the subject of three review articles on quinacridone crystallography.^[17-19] We encountered similar problems, and were unable despite many attempts to grow suitable crystals of Epi using vapor or solution-based methods. These crystals were either very small, in the < 10 μm range, or had multiple twinning defects. However, successful crystal growth was achieved with 2F-Epi and 2Cl-Epi. The materials were first purified twice via temperature-gradient sublimation and then loaded into an alumina crucible and heated to 330-350 $^{\circ}\text{C}$ in a borosilicate glass tube under a 2 L/min flow of dry N_2 gas. Over the course of 3-5 days, large single crystals grew in the downstream 110-130 $^{\circ}\text{C}$ zone of the glass tube. 2Cl-Epi crystals could be measured using $\text{Cu K}\alpha$ radiation on a standard Bruker diffractometer. The smaller 2F-Epi crystals were measured using 0.7 \AA synchrotron radiation. Both materials crystallize in the same fashion: Projections of the crystal structure of 2Cl-Epi are shown in **Figure 2**. The two halogenated derivatives crystallize with a linear-chain H-bonding lattice featuring two-dimensional π - π stacking, very similar to the quinacridone α_{I} phase.^[19] Molecules are H-bonded to two neighbors, forming infinite linear chains which are parallel to each other. These linear chains are π - π stacked on top of each other in a brick-wall pattern. The $\text{NH}\cdots\text{O}=\text{H}$ -bond length is very short: 2F-Epi, (2Cl-Epi, in parenthesis); 2.05 (2.06) \AA , very close to that found in the quinacridone α_{I} phase (2.01 \AA). Indigos, for comparison, have H-bond lengths of 2.1 – 2.8 \AA . Intermolecular distances for stacking interactions are 3.9 \AA (3.69 \AA) along a, and 6.2 \AA (5.97 \AA) along b. As in the case of other H-bonded pigment semiconductors, it is concluded that charge transport primarily occurs perpendicular to the H-bonding plane, along the two π -stacking directions. The short H-bond lengths and close stacking interactions are together accountable for the high crystal lattice energy of epindolidione pigments, as observed by thermogravimetric (TGA) analysis (**Figure 3**). All three epindolidione pigments were found to sublime cleanly with no charred residue, with sublimation temperatures > 405 $^{\circ}\text{C}$. This high sublimation point is indicative of strong intermolecular interactions and high crystal lattice energy. As a reference example, tetracene has an analogous structure and similar molecular weight, but sublimates at 280 $^{\circ}\text{C}$ under the same experimental conditions.^[8] We were not successful to grow diffraction-quality crystals of the tBOC-derivatives epindolidiones, however in the loss of isobutene and CO_2 is found to occur at 190 $^{\circ}\text{C}$, followed by sublimation at the same temperature as the measured

1 unsubstituted epindolidione. This confirms the successful regeneration of H-bonded
2 epindolidione following thermal deprotection.
3

4 2.4 Optical Properties 5

6 Epindolidiones described in the patent literature are pigments with yellow or orange color. All
7 three derivatives described here are yellow powders. The solubility of the epindolidiones is
8 very poor in organic solvents, but they can be dissolved at concentrations $< 200 \mu\text{M}$ in polar
9 aprotic solvents such as DMSO and DMF after heating and sonication. **Figure** a shows the
10 extinction coefficients of Epi, 2F-Epi, 2Cl-Epi dissolved in DMSO. A typical vibronic
11 progression is clear for all compounds. Epindolidiones are isomers of indigo, and contain a
12 very similar cross-conjugated system. For indigo, the cross-conjugated arrangement of
13 electron-rich NH groups with the electron-withdrawing carbonyl functions produces the so-
14 called H-chromophore, which supports a low-energy charge-transfer type absorption.^[7,20] Our
15 observations on the three epindolidione derivatives appear to support the hypothesis that they
16 are indeed H-chromophore systems as well. If epindolidiones are treated as an H-
17 chromophore system like the cross-conjugated indigos, the presence of a π -electron donor
18 *para* to the nitrogen (donor component in the H-chromophore) should shift absorption
19 bathochromically by virtue of increasing the donor ability of the NH groups. This is consistent
20 with the observation that the halogenated compounds have a ~ 10 nm bathochromic shift in
21 absorption onset compared to the unsubstituted Epi. Photoluminescence and excitation spectra
22 for Epi, 2F-Epi, and 2Cl-Epi are shown in panels b, c, and d, respectively, of Figure . While
23 the halogenated derivatives show a typical Franck-Condon mirror-image luminescence
24 spectrum, for unsubstituted Epi the highest energy luminescence peak is weak compared with
25 the next lower-energy PL peak. This is reflected also in the excitation spectrum. The origin of
26 this effect is unclear. The PL yields of epindolidiones in solution are high,^[21] much higher
27 than in the case of indigos. Indigos undergo a photoinduced intramolecular proton transfer,
28 leading to a tautomerization reaction followed by relaxation, leading to overall efficient
29 radiationless internal conversion and very weak photoluminescence ($\phi_f = 1 \times 10^{-3}$).^[7,11] This
30 tautomerization mechanism is blocked in the case of epindolidione by their fused-ring
31 structure. Therefore epindolidiones can be regarded as H-chromophoric molecules without a
32 proton-mediated relaxation pathway and thus high luminescence.
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55

56 In order to better understand the optical properties of epindolidiones, we carried out
57 DFT calculations with a 6-311+g(d,p) basis set. The optimized ground state geometries and
58 charge isodensity plots for the HOMO and LUMO orbitals of the three Epi derivatives are
59
60
61
62
63
64
65

1 shown in **Figure** . The HOMO orbitals are concentrated on an extended conjugated segment
2 consisting of the two nitrogen atoms bridged by the central C=C group, while the LUMO
3 orbitals are shifted to the carbonyl functions and C-C units. This is consistent with the H-
4 chromophore model.^[20,22] Indeed, the calculated plots for epindolidione are very similar to
5 those of indigo itself.^[23] The addition of halogens *para* to the nitrogen groups is thus expected,
6 according to the H-chromophore model, to influence primarily the HOMO. This is seen in the
7 isodensity plots, where indeed charge density is localized over the halogens in the HOMO but
8 not the LUMO orbitals. According to DFT, both HOMO and LUMO energies are lower than
9 in unsubstituted Epi, leading to smaller band gap, which is observed experimentally as well.
10 Vacuum-evaporated thin films of the three Epi derivatives have absorption onsets
11 bathochromically-shifted by about 50 nm relative to solutions (**Figure**). This is characteristic
12 of H-bonded pigments, where close lattice packing leads to a large degree of intermolecular
13 electronic interaction.^[2] Moreover, the effect of supramolecular mesomerism, where sharing
14 of the proton via H-bonding markedly shifts the electronic properties of such molecules, has
15 also been proposed as an explanation for large bathochromic shifts in H-bonded pigments.^[18]
16 The PL of evaporated films features a Stokes-shifted peak in the green, and several peaks far
17 to the red, at 625, 690, and 780 nm for all derivatives. The red-shift for these emissive
18 features is too large to be explained by vibronic replicas, also their oscillator strength is
19 relatively high. Two explanations for these peaks can be put forward: either they originate
20 from extrinsic defect states in the solid-state films, or they are excimeric species. Defect states
21 in such films may arise from impurities, states at grain boundaries between the crystallites, or
22 interfaces between polymorphic forms. It should be stressed that the presence of the low-
23 energy luminescence peaks, as well as their position and relative intensity, was found to be
24 highly reproducible over a wide range of sample preparation conditions. The luminescence
25 features were found to be invariant over evaporation rates of $< 0.1 - 6 \text{ \AA/s}$, substrate
26 temperatures of $25 - 140 \text{ }^\circ\text{C}$, post-deposition annealing, as well as solvent annealing
27 procedures which are known to induce rearrangements in H-bonded pigments.^[24] Based on
28 the lack of effect of processing conditions, and the high purity of the sublimation-purified
29 material, we propose that extrinsic defect state luminescence is not likely responsible for the
30 low-energy emission, but rather true excimeric species. This hypothesis is further supported
31 by fluorescence microscopy of single crystals (Figure S2), where both green and red emission
32 is found to originate from the bulk of the crystals. Both the singlet and excimeric PL features
33 were found to be robust and resistant to degradation under conditions of aging the samples in
34 air, or exposure to water.

2.5 Electrochemical properties

Cyclic voltammetry was carried out on 80 nm thick films of epindolidiones evaporated on ITO-coated glass functioning as the working electrode. A platinum foil was used as the counter electrode and an Ag/AgCl wire as the pseudo-reference electrode. All three derivatives demonstrated reduction and oxidation behavior (**Figure**). Evaluating the reversibility is complicated by the fact that both the reduced and oxidized forms of the epindolidiones are highly-soluble in the polar electrolyte solution. Thus, the smaller currents corresponding to the reverse redox processes are caused, in large part, by the substantially diminished quantity of analyte on/near the working electrode. Reduction appears to be quasi-reversible for all three derivatives, while oxidation not so. Epi showed an oxidation onset at 1200 mV (HOMO = -5.6 eV), 2Cl-Epi at 1350 mV (HOMO = -5.7 eV), and 2F-Epi at 1800mV (HOMO = -5.8 eV). The oxidation potential, not surprisingly, scales with the electronegativity of the halogen substituents. The reduction potential, however, did not display a similar trend. All three derivatives show a reduction peak with an onset of -1500 mV vs. Ag/AgCl, corresponding to a LUMO level of approx. -2.9 eV versus vacuum. This is easy to rationalize due to the 2,8 positions of the halogens on the substituted epindolidione molecules according to the H-chromophore model, as discussed in section 2.3. As the halogens are *para* to the NH groups, they have an inductive withdrawing effect on the electron-rich NH part of the molecule, thereby affecting the oxidation potential markedly. However the halogens have no inductive effect on the carbonyl functional groups of the molecule, which are responsible of the electron-accepting properties of these molecules. From an electrochemical point of view, epindolidiones can be both reduced quasi-reversibly, and oxidized, but they are wide band gap materials with relatively high potentials needed to achieve reduction or oxidation.

2.6 Organic field-effect transistors (OFETs)

2.6.1. Measurement of OFETs

OFETs were fabricated with the three Epi derivatives using a 32 nm-thick anodically-grown AlO_x passivated with a layer of linear-chain hydrocarbon C₄₄H₉₀ (tetratetracontane, or TTC) as described in earlier works.^[7] This composite gate dielectric has a C_{0d} of ~40 nF/cm². Mobility was calculated from the saturation regime.^[25] Top source-drain contacts were evaporated through a shadow mask, giving channel dimensions of W = 2 mm, L = 60 μm. Gold source-drain contacts afforded p-type operation, while aluminum contacts gave n-type

1 behavior. The transfer curve of a typical p-type epindolidione device is shown in **Figure a**.
2 Average devices gave mobilities of $0.2 \text{ cm}^2/\text{Vs}$, though champion devices had mobilities of
3 around $\sim 1 \text{ cm}^2/\text{Vs}$. Smaller channel lengths can be correlated to higher mobilities, as we
4 previously demonstrated for Epi FETs.^[8] With aluminum contacts, Epi showed n-type
5 behavior (Figure b), albeit with a significantly lower mobility of $2 \times 10^{-3} \text{ cm}^2/\text{Vs}$. Based on the
6 LUMO level of -2.9 eV calculated from cyclic voltammetry, it is likely that a significant
7 barrier to electron injection exists and thus contact resistance limits n-type operation. In the
8 case of 2-F Epi (Figure c) and 2-Cl Epi (Figure d), only n-type mobility could be observed.
9 The deep HOMO values resulting from the strong electron affinity of the halogen functional
10 groups, as evidenced from cyclic voltammetry, cause a substantial hole injection barrier.
11 While the electron mobility of 2-Cl Epi was relatively low, $2 \times 10^{-3} \text{ cm}^2/\text{Vs}$, 2F-Epi showed an
12 impressive average electron mobility of $0.1 \text{ cm}^2/\text{Vs}$. From these results it is clear that by
13 simple derivitization of the epindolidione core, both n- and p-type behavior can be obtained.
14 FETs with Epi as the active layer were measured in air over 250 days, with no statistical
15 decline in mobility whatsoever. This correlates with our earlier work,^[8] where samples
16 fabricated as part of that study still operate at the same level after ~ 2 years.
17
18
19
20
21
22
23
24
25
26
27
28
29
30

31 2.6.2 Stability in aqueous environment

32 Motivated by possible applications of stable FETs for bioelectronics applications^[26], we
33 evaluated the stability of Epi FETs in various aqueous environments. To operate under water,
34 high capacitance gate dielectrics must be used to keep operating voltages in the range of 1-2
35 V. We utilized anodic aluminum oxide prepared with an anodization voltage of 5V, giving an
36 AlO_x layer with a thickness of $\sim 8 \text{ nm}$. This layer was then modified by application of an n-
37 octadecyl phosphonic acid self-assembled monolayer, giving a C_{od} of approx. $350 \text{ nF}/\text{cm}^2$.^[27]
38 Devices with top source-drain contacts of gold were used without any passivation layer, thus
39 the Epi/Au surface layer was in direct contact with the water environment. A
40 poly(dimethylsiloxane) rubber block was used to confine the electrolyte over the entire
41 transistor active area, with a volume of $40 \mu\text{L}$ of fluid over the FET device. We utilized a test
42 sequence to evaluate OFET performance in a pH range from 3-10 and in the presence of a
43 wide range of various ionic species. Transfer characteristics were measured over 60 cycles in
44 each of a series of different aqueous environments sequentially using a scan rate of $150 \text{ mV}/\text{s}$
45 (**Figure 9**): $18 \text{ M}\Omega$ high-purity water, pH 7 acetate buffer solution, a pH 7.6 phosphate buffer
46 solution, a pH 4 acetate buffer solution, a pH 3 HCl solution, and a pH 10 NaOH solution.
47 Between measurements the devices were rinsed with deionized water. A total of 360 cycles
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1 were measured in this test, plus 10 cycles for dry samples before and after the assay. Devices
2 measured in air with a $V_{SD} = -0.5V$ exhibited a saturation current of around 100 nA at a $V_G =$
3 $-2.5V$ and an on/off ratio of $\sim 10^3$. After 360 cycles in the different aqueous environments the
4 same performance was found, as can be seen comparing the black trace in the first panel of
5 Figure 8 and the blue trace in the final panel. All the “wet” environments featured an off
6 current about 10 times higher than in the dry state, due to ionic current between source and
7 drain. This current is not dependent on pH, and thus this off-current increase cannot be
8 attributed to doping of the Epi layer but indeed to electrochemical currents in the electrolyte
9 solution. The on current and threshold voltage of the Epi transistors remained constant while
10 cycling under the different electrolyte environments. Previous studies have shown OFETs
11 stable over cycling in pH 7 water^[28], however to our knowledge no study has shown stability
12 in a pH range as wide as that of the present study. This result demonstrating excellent stability
13 in quite demanding aqueous environments suggests that epindolidiones can be highly
14 effective active materials in devices for bioelectronics.
15
16
17
18
19
20
21
22
23
24
25
26

27 2.7 Organic light-emitting diodes (OLEDs)

28 Diodes with the structure ITO/PEDOT:PSS/Epi/Al were fabricated in order to evaluate the
29 electroluminescence spectra of the different epindolidione derivatives. J-V characteristics are
30 shown in **Figure 10a**. The electroluminescence spectra (Figure 10b) of each of the derivatives
31 featured the same S_1-S_0 transitions and excimeric peaks at higher wavelengths as the PL
32 spectra. The combination of green and red electroluminescence led to an overall
33 yellow/orange-colored emission. The CIE 193 chromaticity coordinates were: Epi, (0.60,
34 0.40), 2F-Epi, (0.59, 0.38), 2-Cl Epi, (0.35,0.62). The electroluminescent performance of
35 each material was comparable, with relatively low brightness of 10-25 cd/m^2 . Experimenting
36 with different growth parameters such as substrate temperature (from 30 °C up to 120 °C) and
37 deposition rate (either slow growth of 0.1 Å/s and 5-6 Å/s) demonstrated no changes in either
38 the brightness of the devices or the relative intensities of the singlet vs. excimer emissions,
39 again providing evidence as to intrinsic excimeric species being responsible for the low-
40 energy emission as opposed to extrinsic trap states. To evaluate the air stability of Epi OLEDs,
41 we fabricated devices with the structure ITO/PEDOT:PSS/Epi/PEIE/Au, where PEIE =
42 poly(ethylene imine, ethoxylated), a modification layer providing good electron-injection
43 ability.^[29] The diodes were found to emit while operating in air with a brightness of $\sim 15 cd/m^2$
44 for a period of 3 weeks. The low electroluminescence of these devices is a problem that may
45 be mitigated by optimizing electron and hole injection layers to provide balanced injection of
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

charges to increase radiative recombination in the epindolidione layer. Excimer-emitting materials are nevertheless an interesting concept to achieve polychromic emission from a single semiconducting material, and have been suggested as a possible route to achieving practical white-light emitting OLEDs.^[30]

2.8 Solubilized epindolidiones and solution processing using the latent pigment route

As described in section 2.2, epindolidiones can be functionalized with solubilizing thermolabile tBOC protecting groups. The double-substituted di-tBOC Epi shows solubility up to about 25 mg/ml in solvents like chloroform, toluene, and chlorobenzene. The mono-tBOC derivative, however, was considerably less soluble in these solvents (up to 1 mg/ml max), though still far more soluble than unfunctionalized Epi. Uniform films of di-tBOC Epi could be obtained by spin-casting. Heating these films at 185 °C for 5 minutes was sufficient to achieve complete deprotection and transformation of the pale yellow di-tBOC Epi films into darker yellow films of Epi (**Figure 11a**). The optical properties of the films, *i.e.* absorbance and photoluminescence, were identical to evaporated films. Unfortunately, repeated attempts to fabricate transistors using this method, on a variety of gate dielectric materials, yielded very poor transport. The origin of this problem is not clear, though previous studies on hydrogen-bonded pigments like indigo concluded that orientation of molecules with π - π stacking parallel to the substrate was critical, and this favorable growth is achieved via evaporation on hydrophobic substrates. Diodes with the structure ITO/PEDOT:PSS/Epi/Al could be fabricated however, yielding performance indistinguishable from evaporated diodes. To obtain a pinhole-free film, a 10mg/ml solution of di-tBOC Epi in chloroform was spin cast following heating to 185°C for 5 minutes, and then a second coating followed by heating. The diodes functioned as OLEDs with the same singlet/excimer emission as the vacuum-processed devices. Absorbance spectra in dilute solution of mono-tBOC- and di-tBOC-Epi are shown in comparison with Epi in Figure 11b, with the corresponding photoluminescence spectra in Figure 11c. The absorbance spectra in solution are very similar to one another, while in the luminescence spectra there is a marked red shift in emission proceeding from unsubstituted Epi, mono-tBOC Epi, to di-tBOC Epi. The increased conjugation length across the molecule provided by the carbonyls on the tBOC groups is likely the cause for this red shift. In absorbance spectra of films (Figure 11d), the situation is different than in solution. The unsubstituted H-bonded form of Epi has a ~ 75 nm red shift in absorbance compared to the tBOC derivatives and a significantly higher oscillator

1 strength. This underscores the importance of intermolecular H-bonding for the optical
2 properties of epindolidione in the solid state.
3
4

5 3. Conclusions 6

7 We have evaluated epindolidione and two halogenated derivatives in terms of their
8 applications as organic semiconductors. Epindolidiones are a class of robust H-bonded
9 organic pigments with a simple synthetic preparation which starts from the well-known
10 aniline class of compounds. From a photophysical perspective, they are H-chromophore
11 systems like the closely-related indigos, however with a hypsochromic absorption relative to
12 indigo and a bright luminescence. A distinctive feature of the epindolidiones is strong
13 excimeric emission – thus a yellow material absorbing in the blue can give strong yellow/red
14 photoluminescence. Electrochemically, epindolidiones can be oxidized and quasi-reversibly
15 reduced, albeit with a substantial band gap. This translates to both electron and hole transport
16 in transistor devices with the appropriate choice of source-drain contact metal. Low-voltage
17 FETs fabricated with epindolidione were found to have extraordinary stability in a wide range
18 of electrolyte solutions, wherein devices operated reliably with no degradation over hundreds
19 of cycles. To our knowledge, no other organic semiconducting materials have demonstrated
20 stability in such a wide range (pH 3-10 was measured here with no degradation). Due to their
21 luminescence and ambipolarity, we found that epindolidiones can be used in
22 electroluminescent devices, where the distinctive combination of higher-energy singlet and
23 lower-energy excimeric electroluminescence is observed. Finally, we have presented a
24 technique of introducing transient protection groups (tBOC) in order to disrupt H-bonding and
25 yield a soluble dye form of epindolidiones. This allows solution-processing techniques as well
26 as potentially enables further chemical derivatization. This work demonstrates the potential of
27 this highly-stable pigment as a versatile organic semiconducting material. Research in
28 industry on organic pigments has developed, over the past century, a range of highly-stable
29 heterocyclic systems synthesized from low-cost precursors. This work suggests that more
30 exploration of this materials class as functional materials for modern technological
31 applications is warranted.
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51

52 4. Experimental section 53 54

55 Details on synthetic procedures and materials characterization data are presented in the
56 supplementary information. Evaporation of thin films of the Epi compounds was done using a
57
58
59
60
61
62
63
64
65

1 custom-built organic evaporation system from *Vaksis R&D and Engineering*, allowing precise
2 rate control and substrate heating. For UV-Vis spectra, a Perkin-Elmer Lambda 950
3 spectrometer was used. Spectroscopic-grade DMSO was used for all optical measurements in
4 solutions. PL spectra were recorded on a photomultiplier tube-equipped double-grating input
5 and output fluorometer manufactured by PhotoMed. Electrochemical measurements were
6 carried out in a dry N₂ environment using a Pt foil as counter electrode, an Ag/AgCl wire as a
7 pseudo-reference electrode, and ~80nm films of the Epi compounds vacuum evaporated on
8 ITO as the working electrode. The supporting electrolyte was 0.1 M *n*-tetrabutylammonium
9 hexafluorophosphate in dry acetonitrile. Frontier orbital levels were calculated according to:
10 $E_{\text{HOMO}} = -(E_{[\text{onset, ox. vs. NHE}]} + 4.75)(\text{eV})$; $E_{\text{LUMO}} = -(E_{[\text{onset, red. vs. NHE}]} + 4.75)(\text{eV})$. Measurements
11 were calibrated against ferrocene/ferrocenium redox couple (Fc/Fc⁺). The values of the Fc/Fc⁺
12 vs NHE and NHE vs. vacuum level used in this work were 0.64 and -4.75 V, respectively.^[31]
13 ITO glass slides used for electrochemistry and diode fabrication were cleaned sequentially
14 with acetone, isopropanol, detergent, and DI water, and finally treated with O₂ plasma. Glass
15 slides for OFET fabrication were prepared in the same way. Aluminum/aluminum Oxide/TTC
16 gate structures were prepared according to reported methods.^[32,33] For low-voltage OFETs
17 optimized for operation in aqueous environments, ultrathin aluminum oxide layers (~ 8 nm)
18 were prepared using the potentiostatic method^[27,34] with a 5 V anodization voltage, treated for
19 1 minute in oxygen plasma to active the surface, and passivated with *n*-octadecylphosphonic
20 acid (C18-PA) according to reported methods,^[35] by immersing for 12 hours in a C18-PA
21 5 mM solution in isopropanol. The samples were rinsed with isopropanol and water and then
22 heated *in vacuo* at 110 °C prior to evaporation of the epindolidione semiconductor layer.
23 OFET properties were measured using an Agilent B1500A parameter analyzer in ambient air
24 environment. The quantitative electroluminescence spectra were measured using a Photo
25 Research Spectrascan PR-655. IV measurements were carried out with a Keithley 2600 source
26 measurement unit.
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46

47
48
49
50 [CCDC 1013233 and 1013474 contain the supplementary crystallographic data for this paper.
51 These data can be obtained free of charge from The Cambridge Crystallographic Data Centre
52 via www.ccdc.cam.ac.uk/data_request/cif.]
53
54
55

56 **Supporting Information**

57 Supporting Information is available from the Wiley Online Library or from the author.
58
59
60
61
62
63
64
65

Acknowledgements

We are grateful for support by the Austrian Science Foundation, FWF, within the Wittgenstein Prize of N. S. Sariciftci Solare Energie Umwandlung Z222-N19 and the Translational Research Project TRP 294-N19 “Indigo: From ancient dye to modern high-performance organic electronics circuits”. Italian MIUR – PON project “Molecular Nanotechnologies for Health and Environment-MAAT” (PON02_005633316357 – CUP B31C12001230005) is also acknowledged.


Received: ((will be filled in by the editorial staff))


Revised: ((will be filled in by the editorial staff))

Published online: ((will be filled in by the editorial staff))


- [1] H. Zollinger, *Color Chemistry. Syntheses, Properties and Applications of Organic Dyes and Pigments*; 3rd ed.; Wiley-VCH: Weinheim, 2003; Vol. 43.
- [2] *High Performance Pigments*; Faulkner, E. B.; Schwartz, R. J., Eds.; 2nd ed.; Wiley-VCH: Weinheim, 2009.
- [3] M. Seefelder, *Indigo in culture, science, and technology*; 2nd ed.; ecomed: Landsberg, Germany, 1994.
- [4] K. Hunger, *Rev. Prog. Color. Relat. Top.* **2005**, *35*, 76.
- [5] M. Irimia-Vladu, E. D. Głowacki, P. A. Troshin, G. Schwabegger, L. Leonat, D. K. Susarova, O. Krystal, M. Ullah, Y. Kanbur, M. A. Bodea, V. F. Razumov, H. Sitter, S. Bauer, N. S. Sariciftci, *Adv. Mater.* **2012**, *24*, 375.
- [6] E. D. Głowacki, L. Leonat, G. Voss, M.-A. Bodea, Z. Bozkurt, A. M. Ramil, M. Irimia-Vladu, S. Bauer, N. S. Sariciftci, *AIP Adv.* **2011**, *1*, 042132.
- [7] E. D. Głowacki, G. Voss, N. S. Sariciftci, *Adv. Mater.* **2013**, *25*, 6783.
- [8] E. D. Głowacki, M. Irimia-Vladu, M. Kaltenbrunner, J. Gąsiorowski, M. S. White, U. Monkowius, G. Romanazzi, G. P. Suranna, P. Mastrorilli, T. Sekitani, S. Bauer, T. Someya, L. Torsi, N. S. Sariciftci, *Adv. Mater.* **2013**, *25*, 1563.
- [9] E. D. Głowacki, L. Leonat, M. Irimia-Vladu, R. Schwödiauer, M. Ullah, H. Sitter, S. Bauer, N. Serdar Sariciftci, *Appl. Phys. Lett.* **2012**, *101*, 023305.
- [10] W. Herbst, K. Hunger, *Industrial Organic Pigments*; 3rd ed.; Wiley-VCH: Weinheim, 2004.
- [11] S. Yamazaki, L. Sobolewski, W. Domcke, *Phys. Chem. Chem. Phys.* **2011**, *13*, 1618.
- [12] E. E. Jaffe, *Surf. coatings Int. JOCCA, J. Oil Colour Chem. Assoc.* **1992**, *75*, 24.
- [13] D. S. Kemp, B. R. Bowen, C. C. Muendel, *J. Org. Chem.* **1990**, *55*, 4650.
- [14] U. Schaedeli, J. S. Zambounis, A. Iqbal, Z. Hao, H. Dubas, **1993** EP 0654711
- [15] J. S. Zambounis, Z. Hao, A. Iqbal, *Nature* **1997**, *388*, 131.
- [16] E. D. Glowacki, G. Voss, K. Demirak, M. Havlicek, N. Sunger, A. C. Okur, U. Monkowius, J. Gąsiorowski, L. Leonat, N. S. Sariciftci, *Chem. Commun.* **2013**, *49*, 6063
- [17] G. Lincke, *Dyes Pigments* **2000**, *44*, 101.
- [18] G. Lincke, *Dyes Pigments* **2002**, *52*, 169.
- [19] E. F. Paulus, F. J. J. Leusen, M. U. Schmidt, *CrystEngComm* **2007**, *9*, 131.
- [20] W. Lüttke, H. Hermann, M. Klessinger, *Angew. Chemie Int Ed.* **1966**, *5*, 598.
- [21] W. Tuer, PhD Dissertation, Epindolidione, Epindoline und lineare sowie trigonale Imidazolderivate Neue Materialien mit interessanten Fluoreszenzeigenschaften, Ludwig-Maximilians-University Munich, **2001**.
- [22] H. Sieghold, PhD dissertation: Synthesen und Spektroskopisches Verhalten von heteroanalogen carbonylkindigo-farbstoffen, University of Göttingen, **1973**.

- 1 [23] A. Amat, F. Rosi, C. Miliani, A. Sgamellotti, S. Fantacci, *J. Mol. Struct.* **2011**, 993, 43.
2 [24] J. Mizuguchi, *Berichte der Bunsengesellschaft für Phys. Chemie* **1993**, 97, 684.
3 [25] D. Braga, G. Horowitz, *Adv. Mater.* **2009**, 21, 1473.
4 [26] L. Torsi, M. Magliulo, K. Manoli, G. Palazzo, *Chem. Soc. Rev.* **2013**.
5 [27] A. I. Mardare, M. Kaltenbrunner, N. S. Sariciftci, S. Bauer, A. W. Hassel, *Phys. Status*
6 *Solidi* **2012**, 209, 813.
7 [28] M. E. Roberts, S. C. B. Mannsfeld, N. Queraltó, C. Reese, J. Locklin, W. Knoll, Z.
8 Bao, *Proc. Natl. Acad. Sci. U. S. A.* **2008**, 105, 12134.
9 [29] Y. Zhou, C. Fuentes-Hernandez, J. Shim, J. Meyer, A. J. Giordano, H. Li, P. Winget,
10 T. Papadopoulos, H. Cheun, J. Kim, M. Fenoll, A. Dindar, W. Haske, E. Najafabadi, T.
11 M. Khan, H. Sojoudi, S. Barlow, S. Graham, J.-L. Bredas, S. R. Marder, A. Kahn, B.
12 Kippelen, *Science* **2012**, 336, 327.
13 [30] G. M. Farinola, R. Ragni, *Chem. Soc. Rev.* **2011**, 40, 3467.
14 [31] C. M. Cardona, W. Li, A. E. Kaifer, D. Stockdale, G. C. Bazan, *Adv. Mater.* **2011**, 23,
15 2367.
16 [32] M. Kraus, S. Richler, A. Opitz, W. Brütting, S. Haas, T. Hasegawa, A. Hinderhofer,
17 F. Schreiber, *J. Appl. Phys.* **2010**, 107, 094503.
18 [33] E. D. Głowacki, M. Irimia-Vladu, S. Bauer, N. S. Sariciftci, *J. Mater. Chem. B* **2013**, 1,
19 3742.
20 [34] M. M. Lohrengel, *Mater. Sci. Eng. R* **1993**, 11, 243.
21 [35] M. Kaltenbrunner, T. Sekitani, J. Reeder, T. Yokota, K. Kuribara, T. Tokuhara, M.
22 Drack, R. Schwödiauer, I. Graz, S. Bauer-Gogonea, S. Bauer, T. Someya, *Nature* **2013**,
23 499, 458.
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

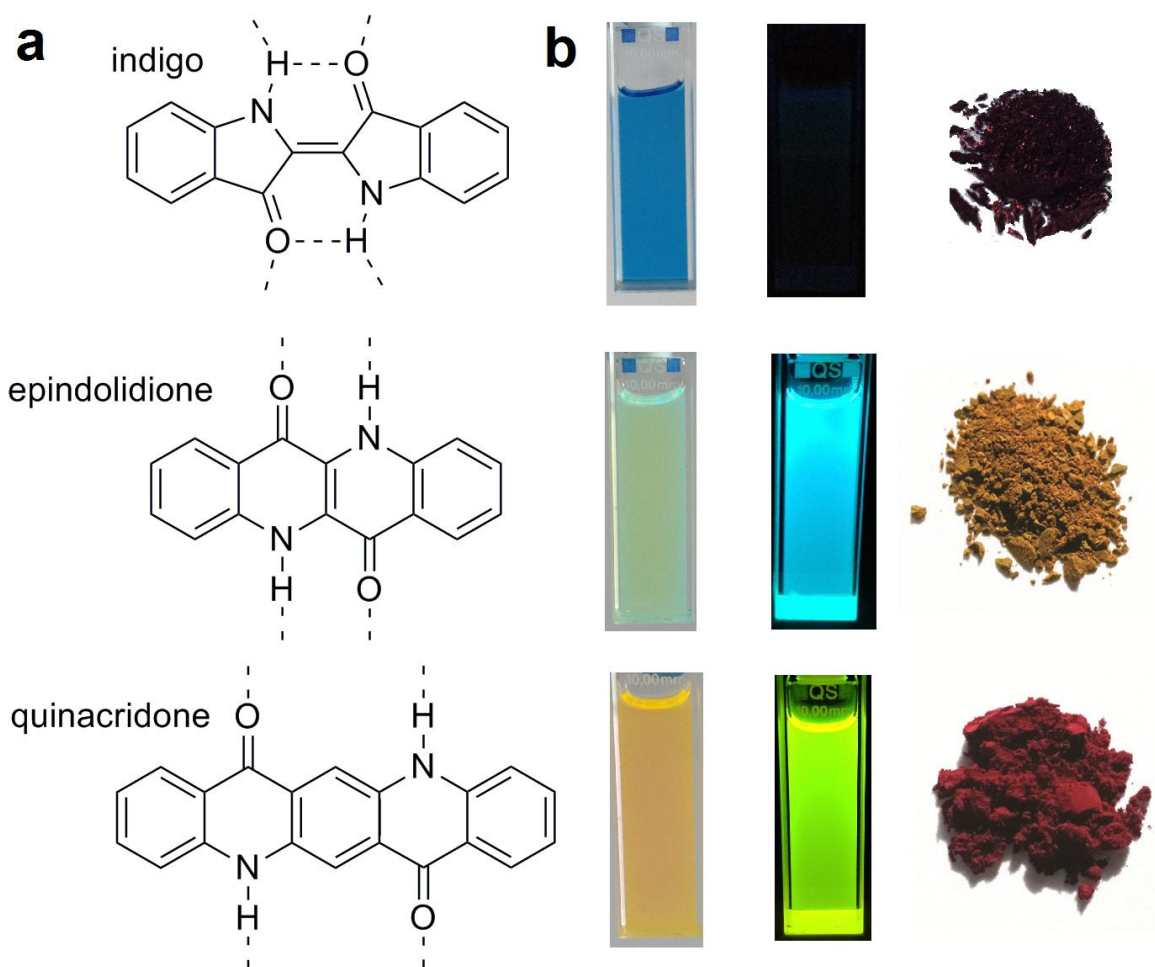

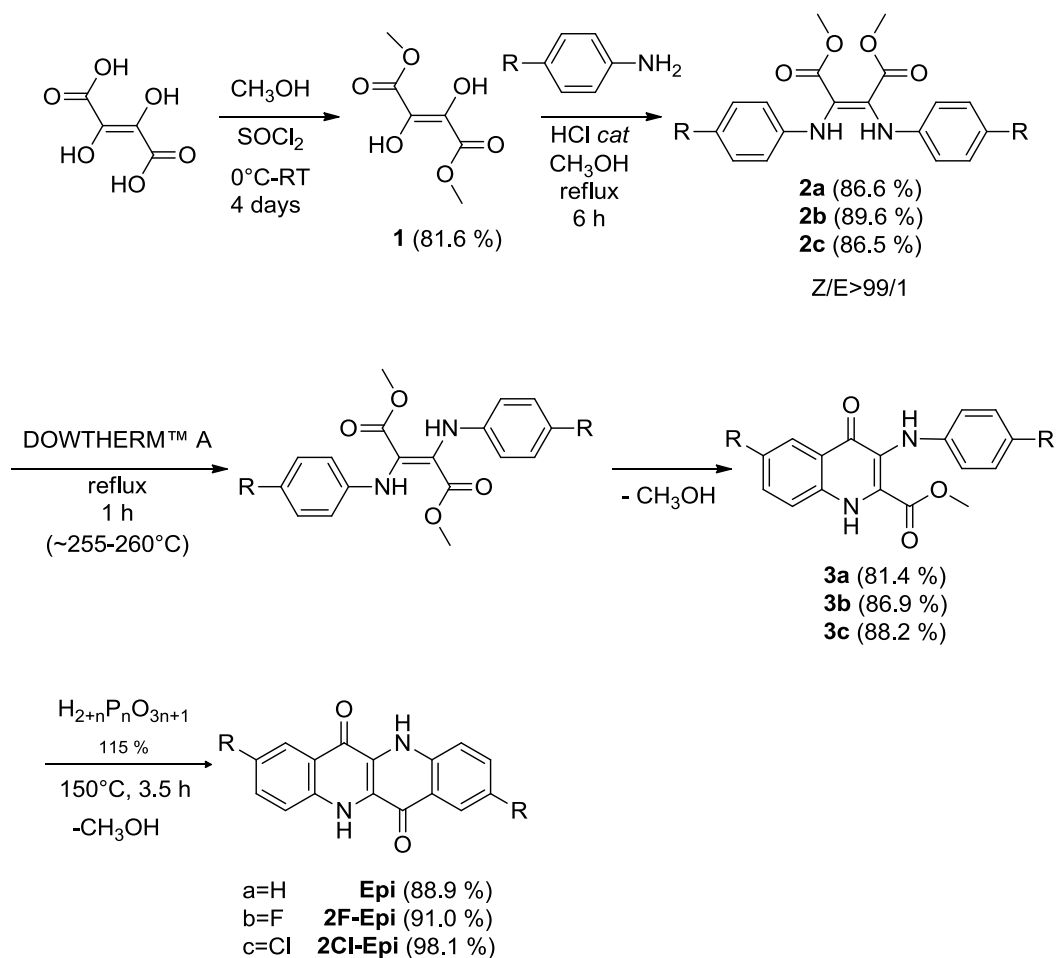

Scheme 1. Synthetic procedure for preparing epindolidiones from *para*-substituted anilines.

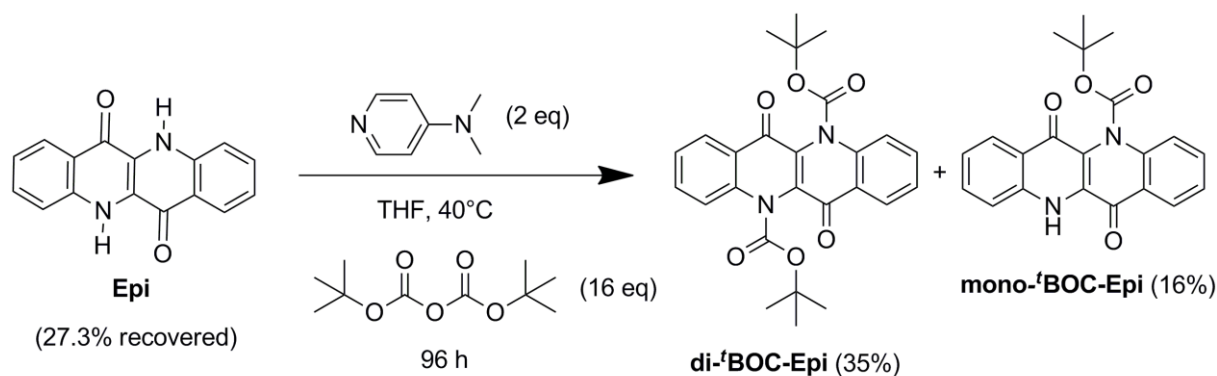

Scheme 2. Protection reaction to obtain tBOC-functionalized epindolidione.

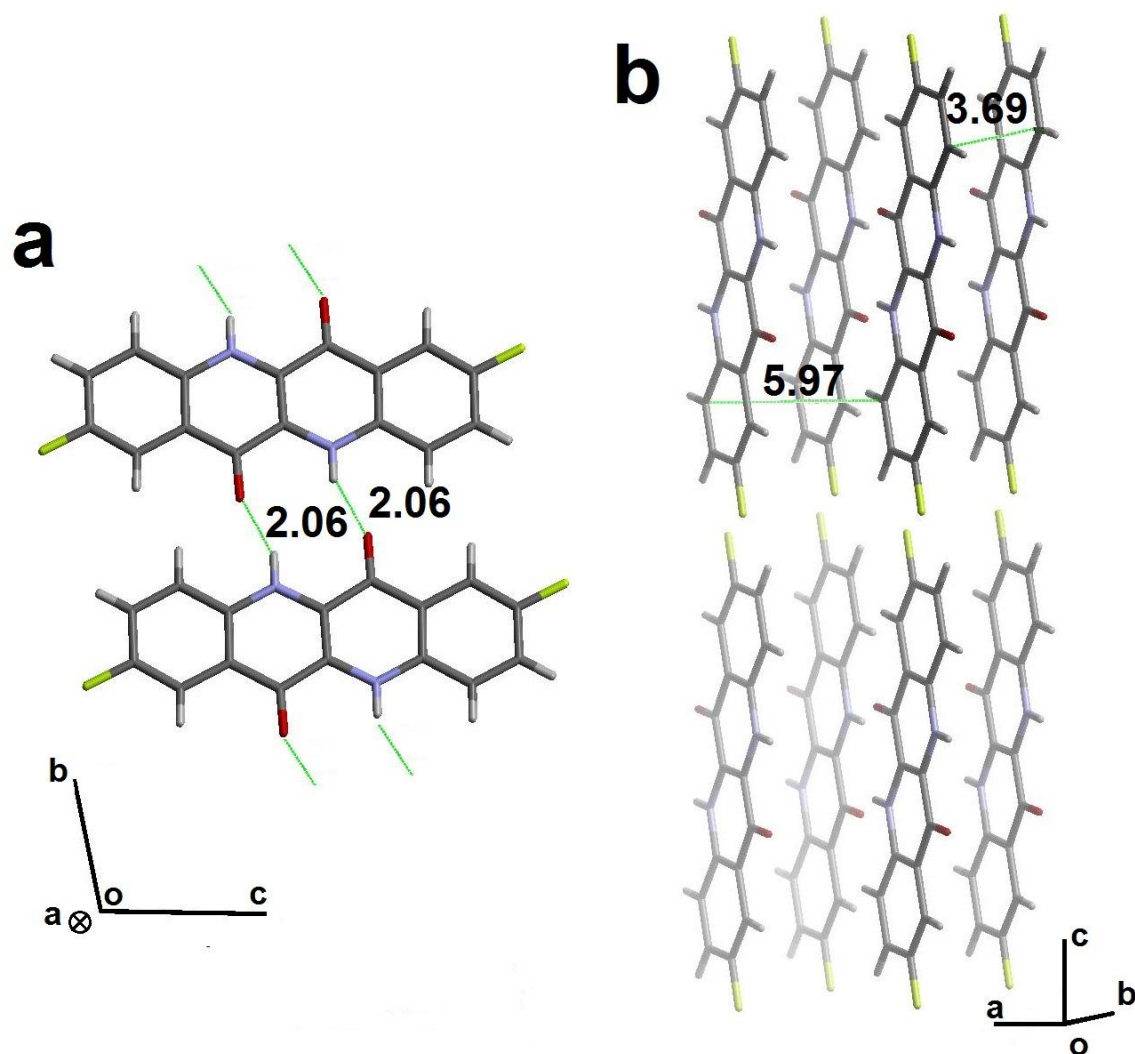


Figure 2. Crystal structure of 2F-Epi obtained from single-crystal X-ray diffraction using synchrotron radiation with a wavelength of 0.7 Å. a) View down the a axis showing the propagation of linear H-bonded chains of molecules. b) View down the b-axis with π - π stacking interactions (with intermolecular distances shown in green). The measured crystal structure of 2Cl-Epi is qualitatively identical to this one.

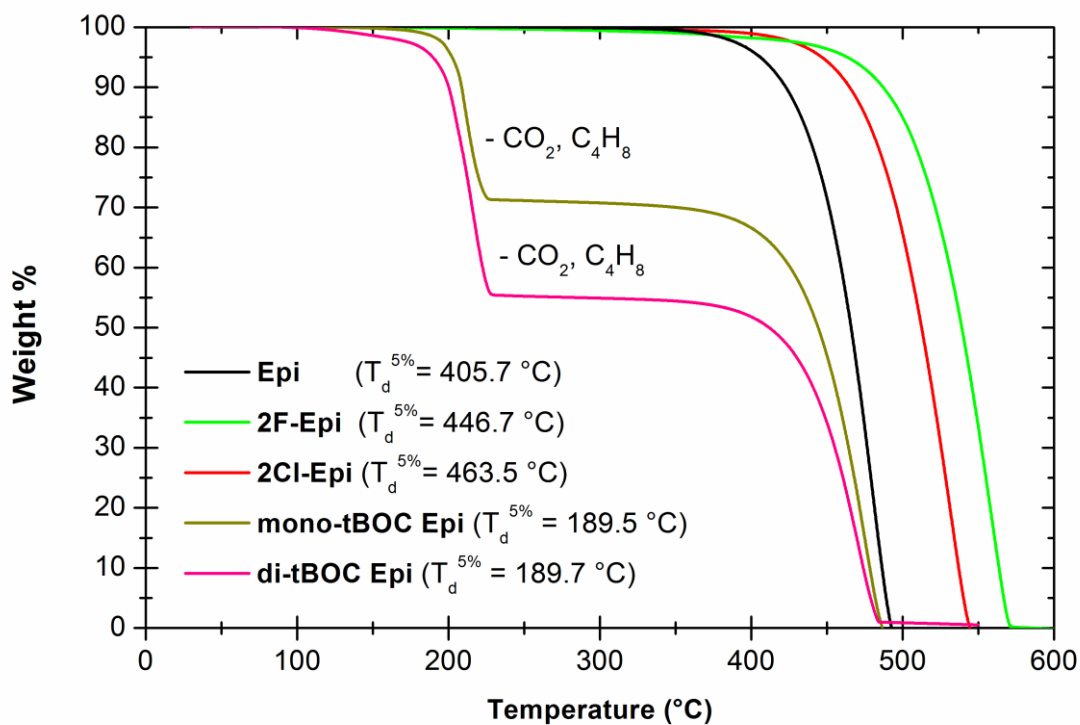


Figure 3. TGA scans for the three epindolidiones and the mono- and di-tBOC epindolidione. In the latter case the loss of carbon dioxide and isobutene is clearly visible.

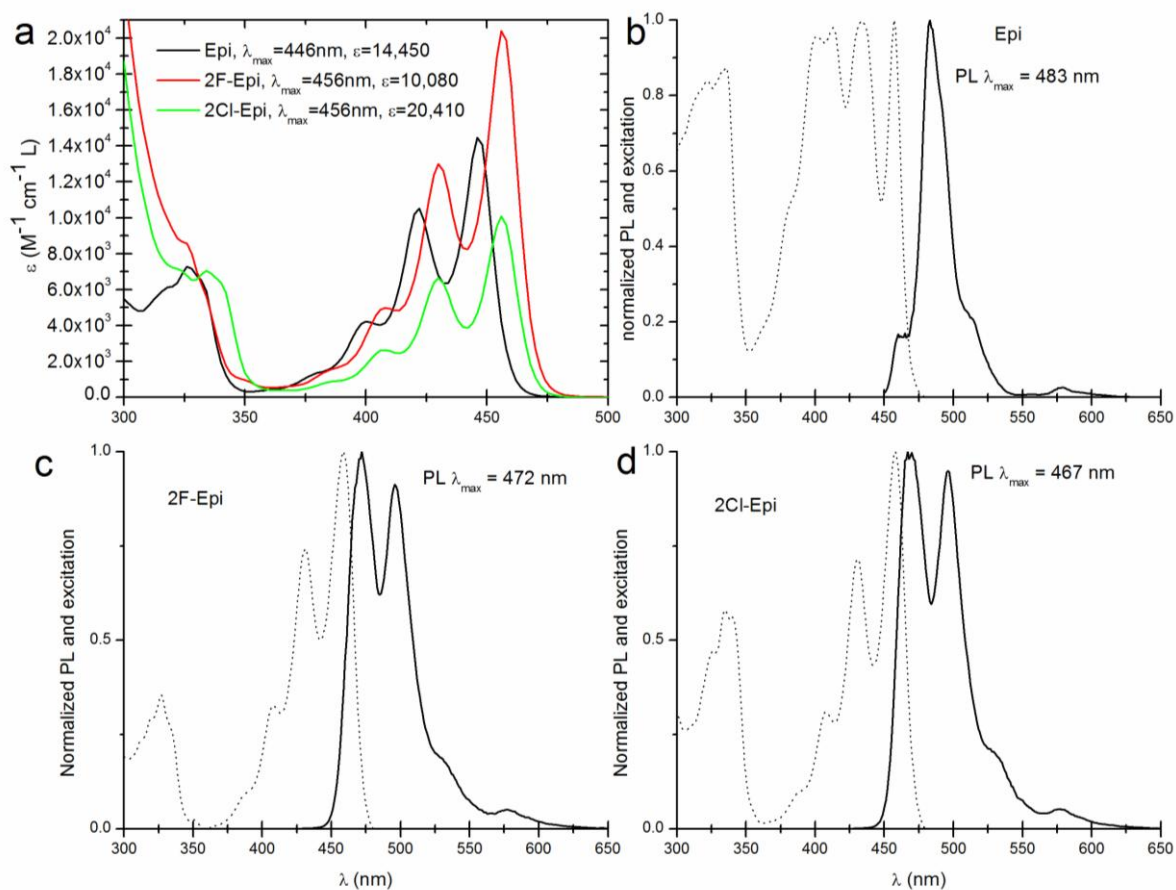


Figure 4. a) UV-Vis absorption and photoluminescence of 0.1 mM solutions of the three epindolidiones in DMSO. b) PL and excitation spectra for 0.1 mM Epi in DMSO. c) PL and excitation spectra for 0.1 mM 2F-Epi in DMSO. c) PL and excitation spectra for 0.1 mM 2Cl-Epi in DMSO

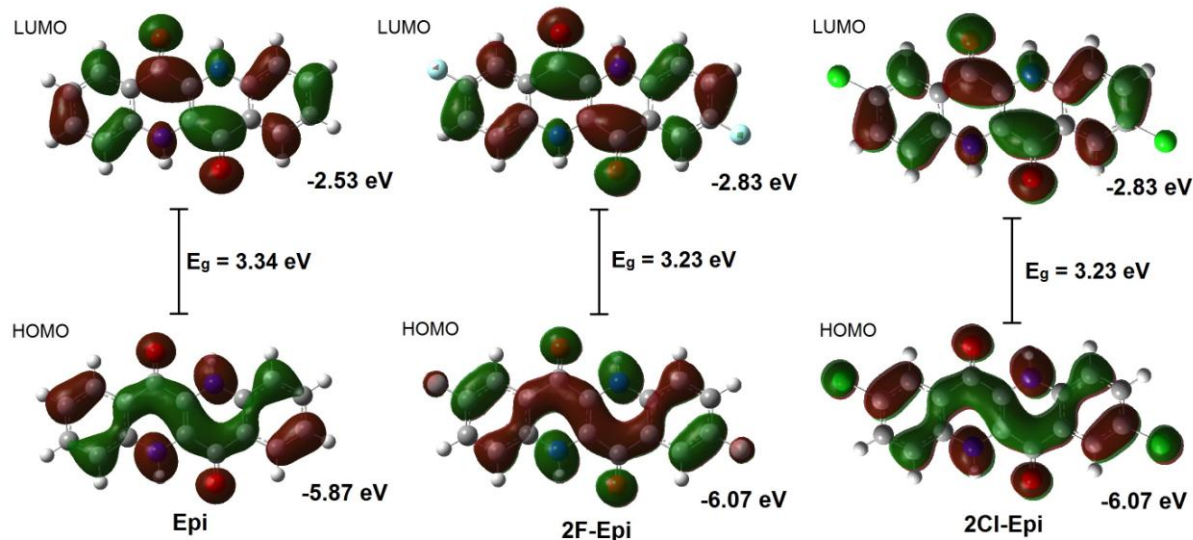


Figure 5. Optimized ground-state geometries and frontier orbital energies of epindolidione and the two halogenated derivatives.

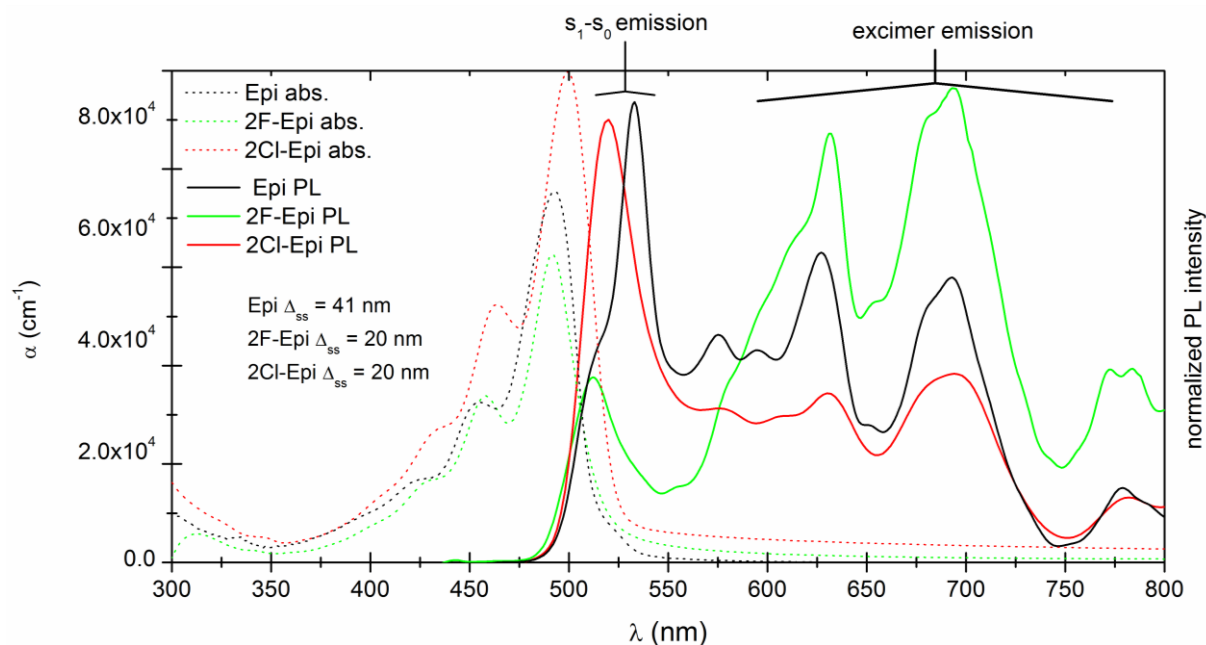


Figure 6. UV-Vis absorption and photoluminescence of the three epindolidiones deposited on glass slides.

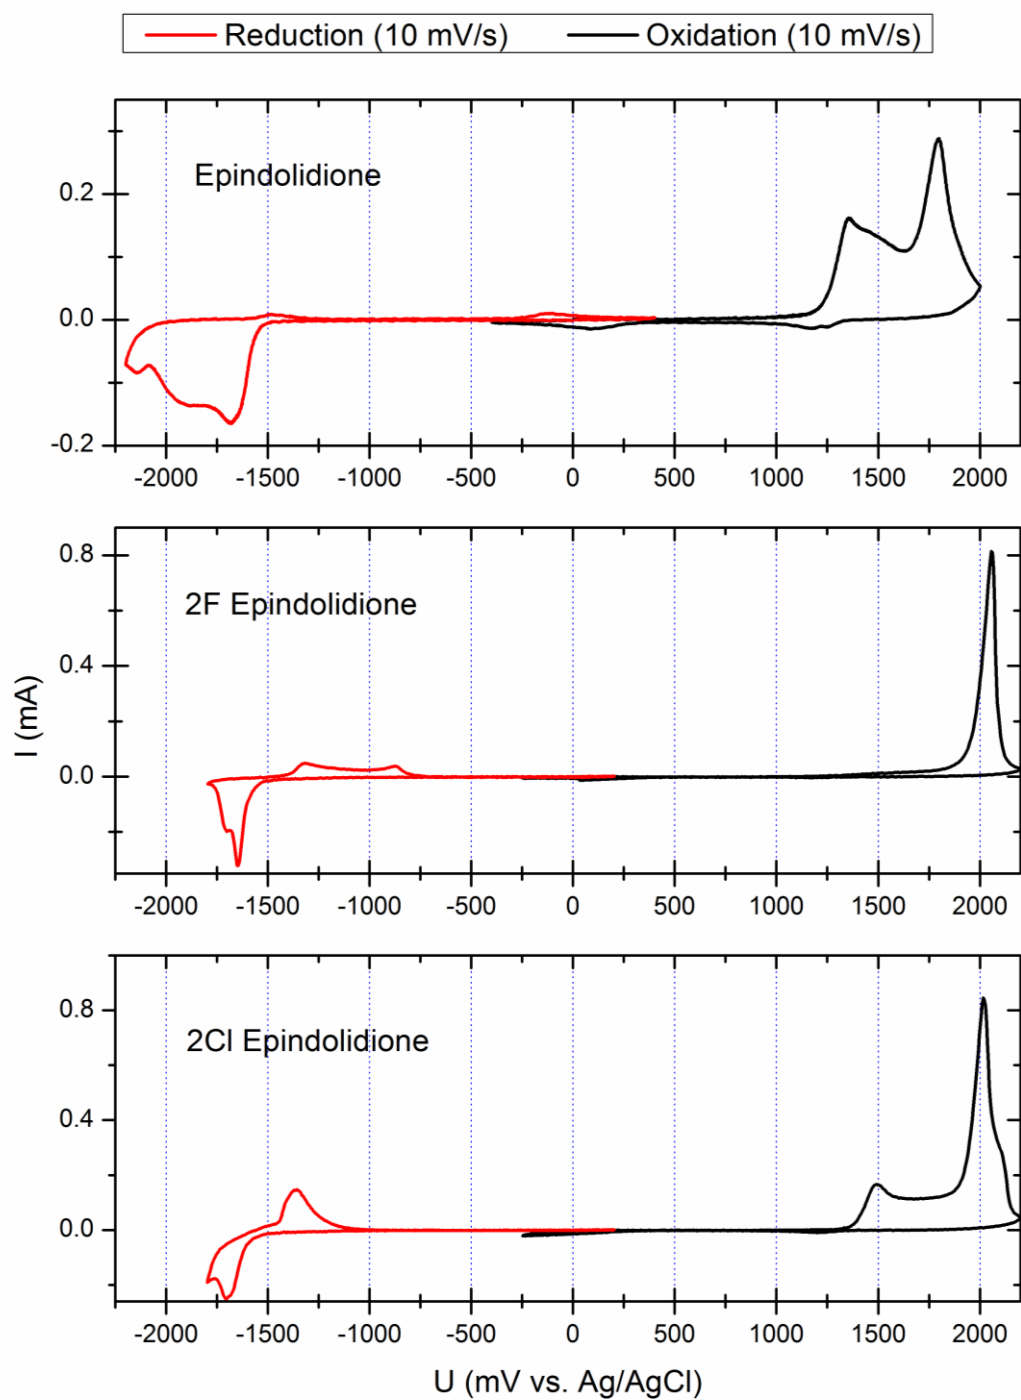


Figure 7. Cyclic voltammety scans of thin films of different epindolidiones deposited on ITO functioning as the working electrode.

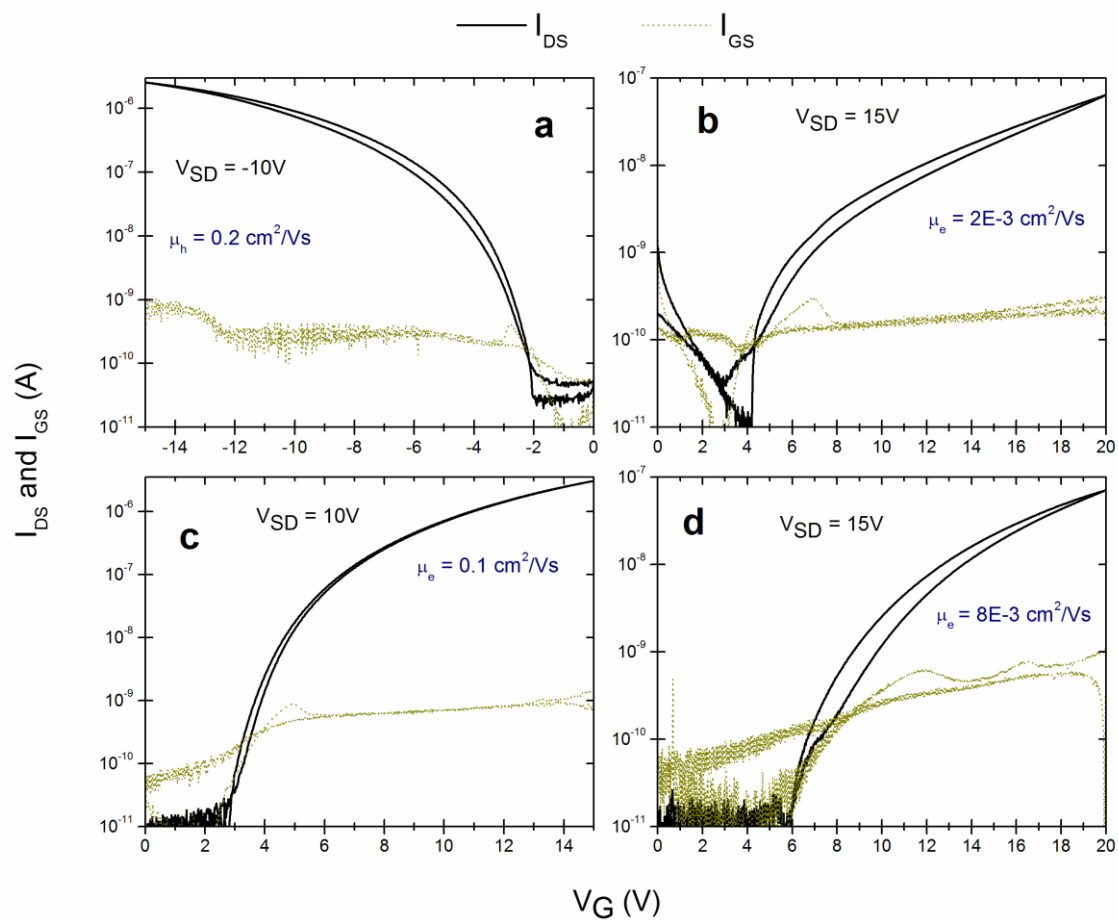


Figure 8. OFET transfer characteristics for a) Epi p-channel with Au source-drain electrodes, b) Epi n-channel with Al source-drain electrodes c) 2F-Epi n-channel with Al electrodes and d) 2Cl-Epi n-channel with Al source-drain electrodes.

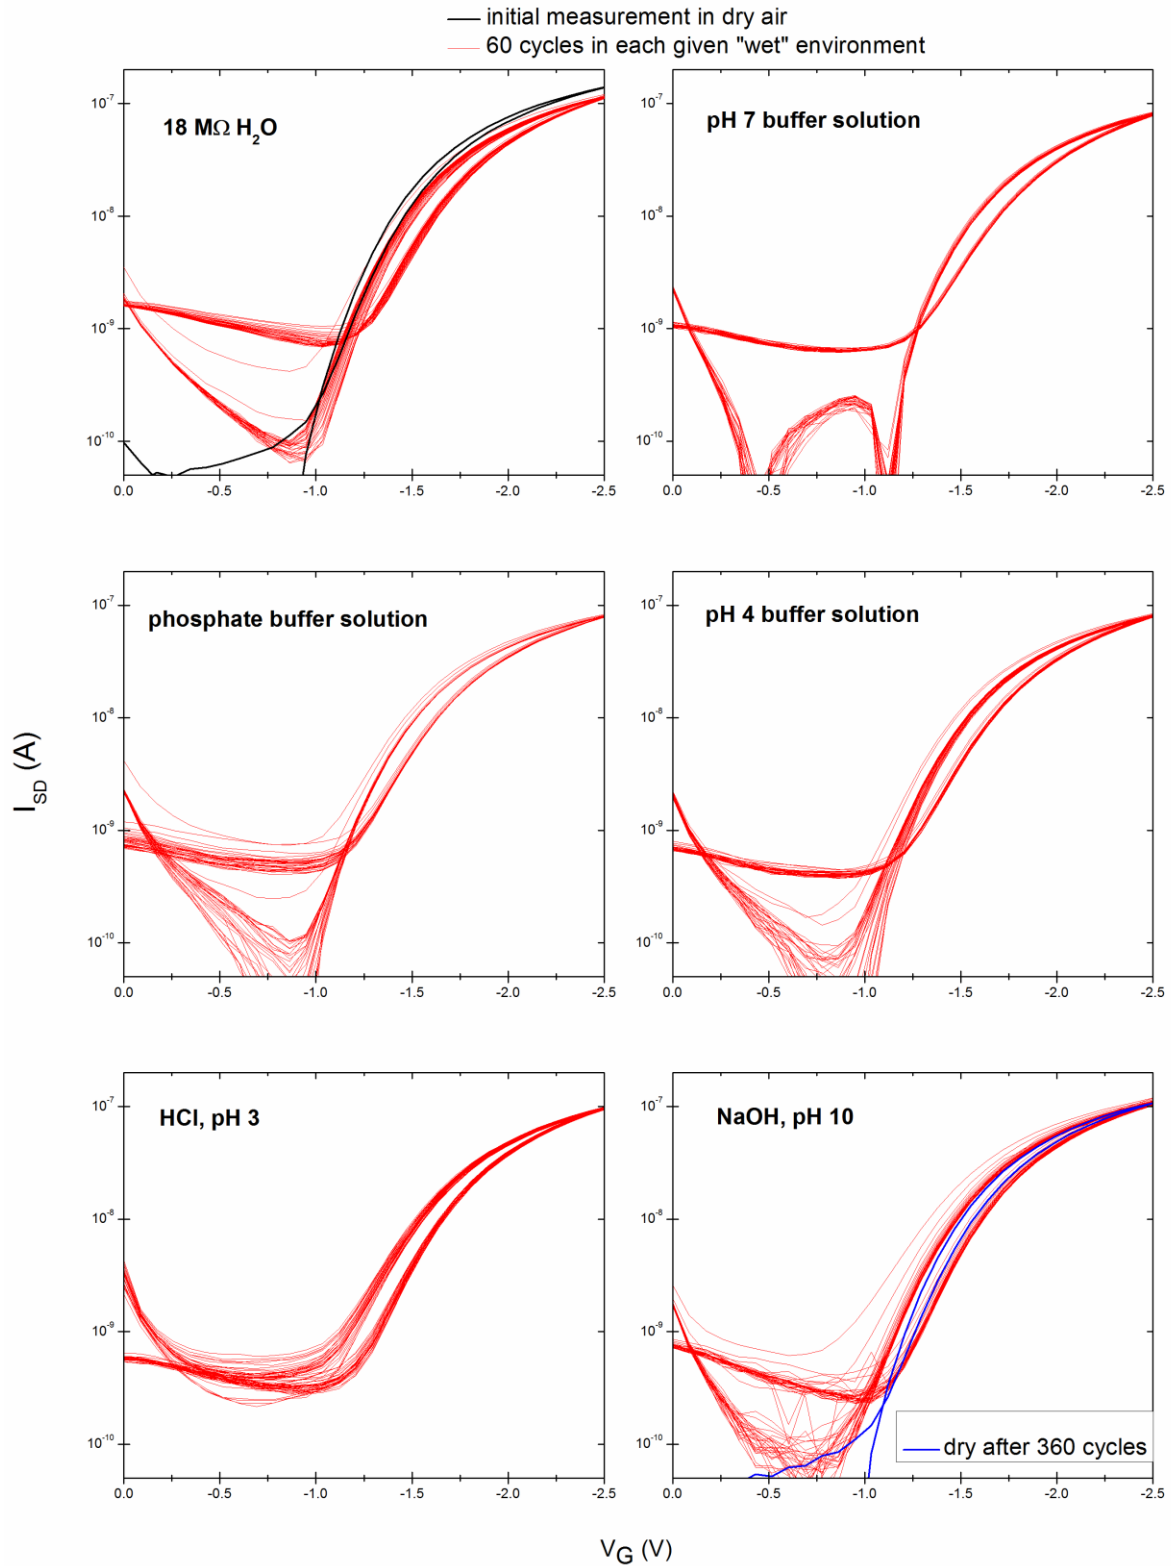


Figure 9. Low-voltage Epi transistor measured in air (black curve) and then 360 cycles in six different aqueous environments successively, with 60 cycles carried out in each. $V_{SD} = -0.5$ V. Samples were rinsed with deionized water between different electrolytes.

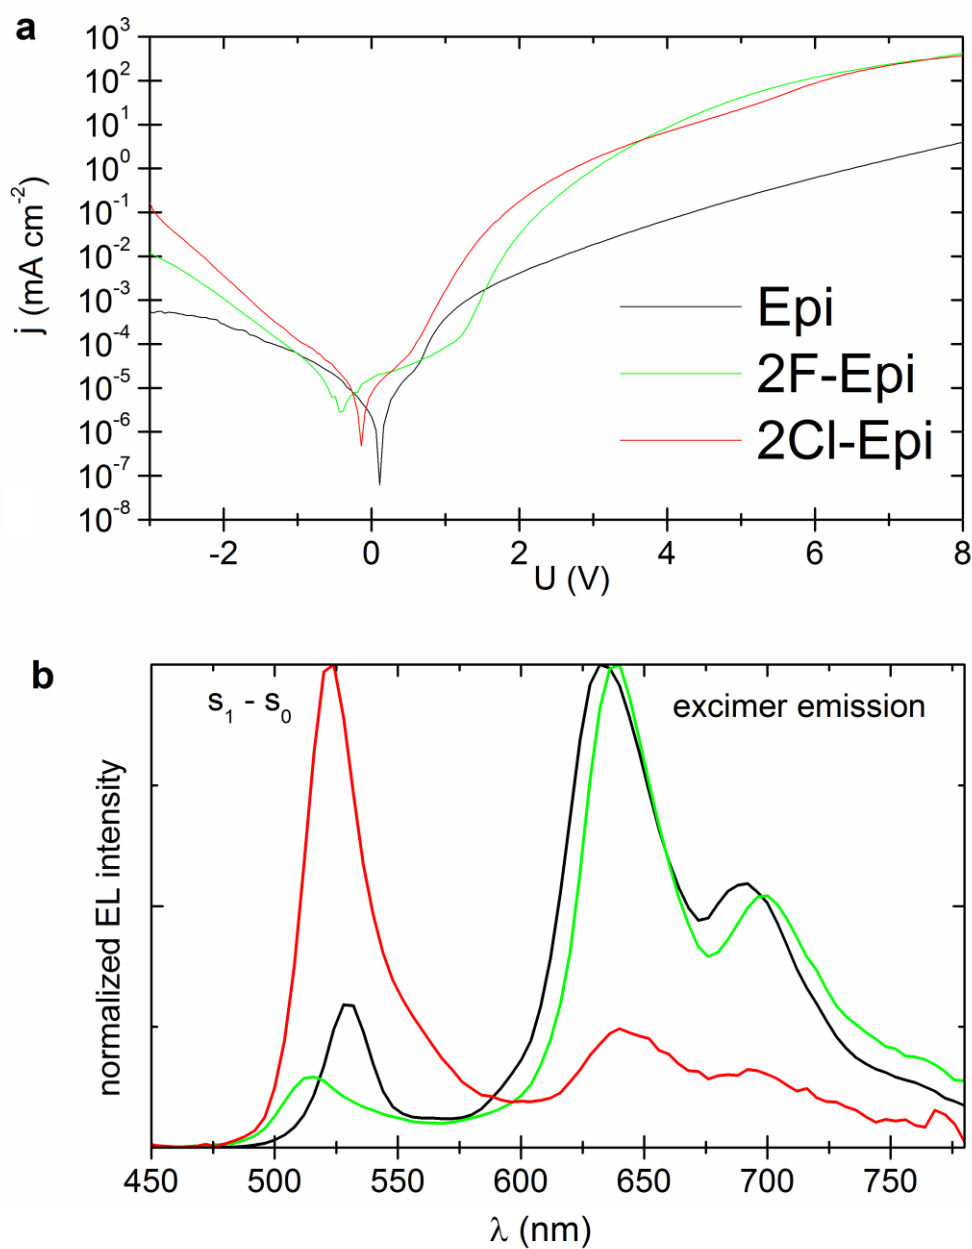


Figure 10. a) J-V characteristics of ITO/PEDOT:PSS/(Epi derivative)/Al diodes. b) Electroluminescence spectra of the same diodes operated in forward bias. Both the S₁-S₀ transition emitting green light and the excimers emitting yellow/red light can be observed.

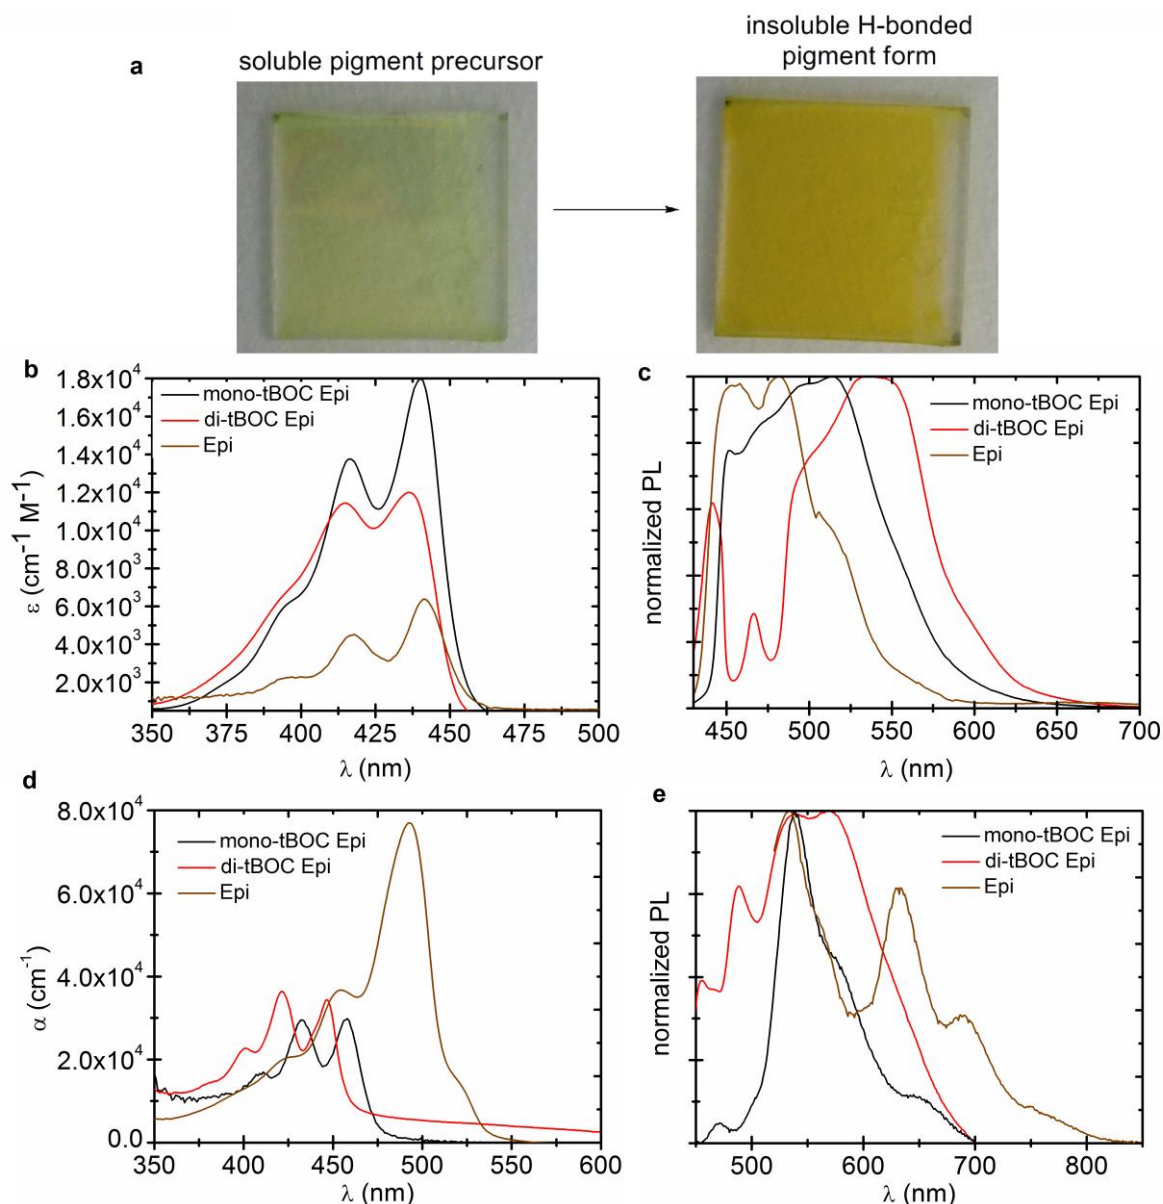


Figure 11. a) A spin-coated film on ITO-glass of di-tBOC Epi before and after thermal conversion into Epi. b) Comparison of extinction coefficients of Epi, mono-tBOC Epi, and di-tBOC-Epi in dilute chloroform solution. c) photoluminescence of the same chloroform solutions. d) Absorbance of thin films of mono-tBOC Epi, di-tBOC Epi, and Epi after thermal conversion deposited on fused silica. e) Photoluminescence spectra of the same films.


TOC:

1 **Epindolidiones are H-bonded organic pigment semiconductors** with excellent operational
2 stability, including in aqueous media. We report on their crystal structure, electrochemical
3 properties, and photophysics, which are dominated by excimeric effects. Transistor and light-
4 emitting devices are demonstrated. We explore routes for solution processing of
5 epindolidiones using transient solubilizing groups.
6

7
8 **Keywords: Hydrogen-bonded pigments, organic semiconductors, indigoids, organic**
9 **field-effect transistors**
10

11
12
13 E. D. Głowacki*, G. Romanazzi, C. Yumusak, H. Coskun, U. Monkowius, G. Voss, M.
14 Burian, R. T. Lechner, N. Demetri, G. J. Redhammer, N. Sünger, G. P. Suranna, N. S.
15 Sariciftci
16

17
18 **Epindolidiones – versatile and stable hydrogen-bonded pigments for organic field-effect**
19 **transistors and light-emitting diodes**
20

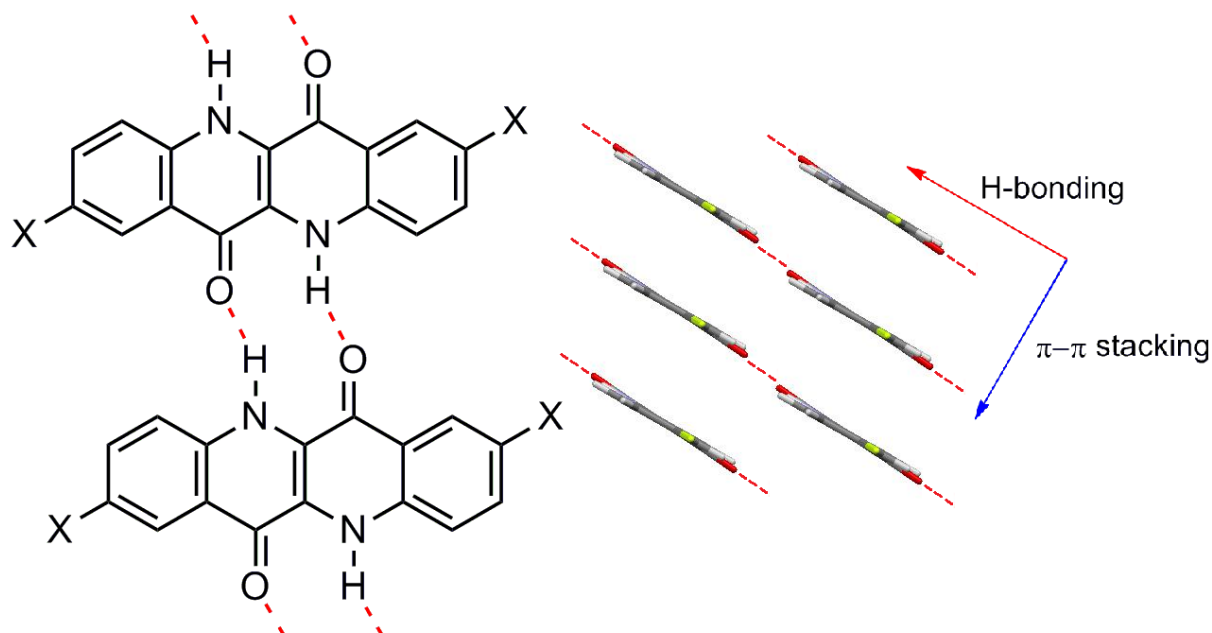

Supporting Information

Epindolidiones – versatile and stable hydrogen-bonded pigments for organic field-effect transistors and light-emitting diodes

*E. D. Głowacki**, *G. Romanazzi*, *C. Yumusak*, *H. Coskun*, *U. Monkowius*, *G. Voss*, *M. Burian*,
R. T. Lechner, *N. Demetri*, *G. J. Redhammer*, *N. Sünger*, *G. P. Suranna*, *N. S. Sariciftci*

Materials and synthetic methods

Reactants were purchased from Sigma-Aldrich® and used without further purification. All manipulations were carried out under inert nitrogen atmosphere using standard Schlenk techniques unless otherwise specified. All solvents used were carefully dried and freshly distilled according to standard laboratory practice. Flash column chromatography was performed using Merck® Kieselgel 60 (230–400 mesh) silica gel. ¹H NMR, ¹³C{¹H} NMR and ¹⁹F NMR spectra were recorded on a Bruker Avance III 700 MHz or Bruker Avance 400 MHz and are reported in ppm relative to tetramethylsilane. FT-IR spectra (in KBr pellets) were recorded on a Jasco FT/IR 4200 spectrophotometer. Melting points were determined on a Büchi B-545 melting point apparatus and are uncorrected. Elemental analyses were obtained on a EuroVector CHNS EA3000 elemental analyser using acetanilide as analytical standard material. The high resolution mass spectrometry (HRMS) analysis was performed using a Bruker microTOF Q II mass spectrometer equipped with an electrospray ion source operated in positive ion mode. The sample solutions (CH₃OH) were introduced by continuous infusion with a syringe pump at a flow rate of 180 μL min⁻¹. The instrument was operated with end-plate offset and capillary voltages set to -500 V and -4500 V respectively. The nebulizer pressure was 0.4 bar (N₂), and the drying gas (N₂) flow rate was 4.0 L min⁻¹. The capillary exit and skimmer voltages were 90 V and 30 V respectively. The drying gas temperature was set at 180°C. The calibration was carried out with a sodium formate solution (10 mM NaOH in isopropanol/water 1:1 (+0.2% HCOOH)) and the software used for the simulations was

1 Bruker Daltonics DataAnalysis (version 4.0). Thermogravimetric analyses (TGA) were
2 performed in a nitrogen flow (40 mL min⁻¹) with a Perkin-Elmer Pyris 6 TGA in the range
3
4 from 30 to 800 °C with a heating rate of 10 °C min⁻¹. Triplicate TGA runs have been
5
6 performed to ensure reproducibility.
7
8
9

10 11 **Synthesis**

12
13 *Dimethyl Dihydroxyfumarate (1)*. To a solution of dihydroxyfumaric acid (13.26 g, 89.55
14 mmol) in anhydrous methanol (70 mL) kept under stirring at 0°C, thionyl chloride (13.4 mL,
15 ~184 mmol) was slowly added dropwise within 15 min. Subsequently, the mixture was
16 allowed to reach room temperature and kept under vigorous stirring for 4 days. The
17 precipitation of an off-white solid was observed. The solid was collected on a sintered glass
18 filter (G4) and was washed with cold methanol (20 mL) then with water (80 mL) and
19 eventually dried under vacuum at 60°C to afford **1** (12.87 g, 81.6 %) as a white solid. mp=
20 175–180°C (lit.^[1] 168–172°C, lit.^[2] 177–179°C, lit.^[3] 165–173°C). ¹H NMR (700 MHz,
21 CDCl₃, δ): 9.43 (s, 2H), 3.89 (s, 6H). ¹³C{¹H} NMR (176 MHz, CDCl₃, δ): 168.04, 135.19,
22 53.15. IR (KBr) ν= 3376, 3178, 3013, 2962, 2850, 1670, 1460, 1443, 1399, 1252, 1023,
23 880, 774, 709, 693, 551 cm⁻¹. HRMS (ESI) *m/z*: [M + Na]⁺ calcd for C₆H₈O₆Na, 199.0213;
24 found, 199.0219 (-2.9 ppm). Anal. calcd for C₆H₈O₆: C 40.92, H 4.58; found: C 40.80, H
25 4.61.
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51

52
53 [1] E. E. Jaffe, H. Matrick, *J. Org. Chem.* **1968**, *33*, 4004–4010.

54 [2] D. S. Kemp, B. R. Bowen, C. C. Muendel, *J. Org. Chem.* **1990**, *55*, 4650–4657.

55 [3] S. Goodwin, B. Witkop, *J. Amer. Chem. Soc.* **1954**, *76*, 5599–5603 and the reference
56
57
58
59
60 therein.

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

Dimethyl 2,3-bis(phenylamino)maleate (2a). 0.65 mL (~7.8 mmol) of concentrated HCl were added to a mixture of **1** (11.10 g, 63.0 mmol) and aniline (12.96 g, 139.2 mmol) in methanol (50 mL). The mixture was stirred under reflux. About 1 h was required for complete solubilisation, and shortly afterwards the precipitation of a yellowish-white solid was observed. After 5 h the reaction mixture was slowly cooled to room temperature and then filtered through a sintered glass filter (G4). The collected solid was washed with cold methanol (3x150 mL) and then dried under vacuum at 60°C to afford **2a** (18.02 g, 86.6 %) as white solid. mp=189.3±0.7°C (lit.^[1] 196–198°C, lit.^[4] 172°C). ¹H NMR (700 MHz, CDCl₃, δ): 7.25-7.22 (m, 4H), 6.98-6.95 (m, 2H), 6.87 (d, J=8.4 Hz, 4H), 5.85 (s, 2H), 3.76 (s, 6H). ¹³C{¹H} NMR (176 MHz, CDCl₃, δ): 165.21, 141.81, 129.34, 125.11, 122.34, 117.80, 52.36. IR (KBr) ν= 3340, 3289, 3042, 3019, 2989, 2946, 1732, 1681, 1591, 1572, 1500, 1474, 1439, 1424, 1381, 1332, 1286, 1242, 1224, 1193, 1173, 1144, 1036, 958, 794, 750, 707, 695 cm⁻¹. HRMS (ESI) *m/z*: [M + Na]⁺ calcd for C₁₈H₁₈N₂O₄Na, 349.1159; found, 349.1153 (+1.8 ppm). Anal. calcd for C₁₈H₁₈N₂O₄: C, 66.25; H, 5.56; N, 8.58; found: C 65.95, H 5.60, N, 8.53.

Dimethyl 2,3-bis((4-fluorophenyl)amino)maleate (2b). The synthesis of **2b** was carried out by the following the procedure reported for **2a** using 1.775 g (10.08 mmol) of **1**, 2.650 g (23.85 mmol) of 4-fluoroaniline, 110 μL (~ 1.3 mmol) of concentrated HCl and 11 mL of methanol respectively. The product **2b** (3.273 g, 89.6 %) was isolated as white solid. mp=199.4±1.7°C (lit.^[1] 196–198°C). ¹H NMR (700 MHz, CDCl₃, δ): 6.96-6.92 (m, 4H); 6.85-6.81(m, 4H); 5.76 (s, 2H); 3.74 (s, 6H). ¹⁹F NMR (376 MHz, CDCl₃, δ): -120.87 (m, 2F). IR (KBr) ν=3330, 3275, 3087, 3062, 3037, 2988, 2951, 1733, 1678, 1604, 1574, 1501, 1484, 1464, 1435, 1400, 1380, 1336, 1287, 1212, 1144, 1092, 1034, 956, 853, 831, 820, 780, 749, 712,

[4] A. Salmony, H. Simonis, *Chem. Ber.* **1905**, *38*, 2580–2601.

664, 641, 559, 526 cm^{-1} . HRMS (ESI) m/z : $[\text{M} + \text{Na}]^+$ calcd for $\text{C}_{18}\text{H}_{16}\text{F}_2\text{N}_2\text{O}_4\text{Na}$, 385.0970; found, 385.0982 (-1.7 ppm). Anal. calcd for $\text{C}_{18}\text{H}_{16}\text{F}_2\text{N}_2\text{O}_4$: C, 59.67; H, 4.45; N, 7.73; found: C 59.36, H 4.41, N, 7.60.

Dimethyl 2,3-bis((4-chlorophenyl)amino)maleate (2c). The synthesis of **2c** was carried out following the procedure reported for **2a** using 1.756 g (9.97 mmol) of **1**, 2.905 g (22.77 mmol) of 4-chloroaniline, 100 μL (~ 1.2 mmol) of concentrated HCl and 10 mL of methanol respectively. The product **2c** (3.400 g, 86.5 %) was isolated as yellowish-white solid. mp=206.5 \pm 0.2 $^\circ\text{C}$ (lit.^[1] 203–204 $^\circ\text{C}$). ^1H NMR (700 MHz, CDCl_3 , δ): 7.21-7.18 (m, 4H), 6.80-6.74 (m, 4H), 5.78 (s, 2H), 3.76 (s, 6H). $^{13}\text{C}\{^1\text{H}\}$ NMR (176 MHz, CDCl_3 , δ): 164.88; 140.16; 129.37; 127.67; 124.97; 119.11; 52.53. IR (KBr) ν =3328, 3273, 3023, 2990, 2946, 2846, 1732, 1679, 1590, 1572, 1493, 1438, 1332, 1239, 1225, 1192, 1146, 1095, 1035, 1013, 958, 852, 821, 798, 767, 755, 715, 672, 652, 637, 609, 545 cm^{-1} . HRMS (ESI) m/z : $[\text{M} + \text{Na}]^+$ calcd for $\text{C}_{18}\text{H}_{16}\text{Cl}_2\text{N}_2\text{O}_4\text{Na}$, 417.0379; found, 417.0367 (+2.5 ppm). Anal. calcd for $\text{C}_{18}\text{H}_{16}\text{Cl}_2\text{N}_2\text{O}_4$ C, 54.70; H, 4.08; N, 7.09; found: C 54.37, H 4.02, N, 7.20.

2-Methoxycarbonyl-3-phenylamino-4-quinolone (3a). In a 1-L round-bottom flask equipped with a Dean-Stark apparatus, a mixture of Dowtherm™ A ^[5] (260 mL) and **2** (16.15 g, 49.49 mmol) was vigorously stirred and heated to reflux (approx. 255-260 $^\circ\text{C}$) within 30 min. The reaction was prolonged for further 30 min, subsequently slowly cooled to room temperature and decanted for 18 h. The precipitation of a brownish-yellow solid product was observed.

The solid was collected on a sintered glass filter (G4), and washed (3x100 mL) with

[5] DOWTHERM™ A heat transfer fluid is a eutectic mixture of two very stable compounds, biphenyl (26.5%_w) and diphenyl oxide (73.5%_w). These compounds have practically the same vapor pressures, so the mixture can be handled as if it were a single compound.

1 petroleum ether (bp 40-60°C). Eventually, the solid was dried under vacuum at 60°C
2 affording **3a** (9.42 g, 79.4 %) as yellow powder. mp=207.2±0.2°C (lit.^[1] 201.5–203°C). ¹H
3 NMR (700 MHz, DMSO-*d*₆, δ): 11.84 (br s, 1H); 8.12 (ddd, J=8.2, 1.5, 0.45 Hz, 1H), 7.86-
4 7.84 (m, 1H), 7.62 (ddd, J=8.6, 6.7, 1.5 Hz, 1H), 7.46 (s, 1H), 7.33-7.30 (m, 1H), 7.12-7.09
5 (m, 2H), 6.74-6.70 (m, 3H), 3.68 (s, 3H). ¹³C{¹H} NMR (176 MHz, DMSO-*d*₆, δ): 173.60,
6 163.45, 145.54, 138.44, 131.85, 129.10, 128.37, 125.21, 124.93, 123.02, 122.79, 118.99,
7 118.67, 115.36, 52.64. IR (KBr) ν= 3376, 3072, 2950, 1735, 1710, 1624, 1603, 1560, 1525,
8 1498, 1476, 1450, 1440, 1384, 1362, 1325, 1304, 1267, 1227, 1174, 965, 770, 756, 697, 532
9 cm⁻¹. HRMS (ESI) *m/z*: [M + Na]⁺calcd for C₁₇H₁₄N₂O₃Na, 317.0897; found, 317.0902 (−1.5
10 ppm). Anal. calcd for C₁₇H₁₄N₂O₃: C, 69.38; H, 4.79; N, 9.52; found: C 69.02, H 4.83, N,
11 9.46.
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28

29 *2-Methoxycarbonyl-3-((4-fluorophenyl)amino)-6-fluoro-4-quinolone (3b)*. The synthesis of
30 **3b** was carried out following the procedure reported for **3a** using 2.920 g (8.06 mmol) of **2b**
31 and 44 mL of Dowtherm™ A respectively. The product **3b** (2.314 g, 86.9 %) was isolated as
32 yellow solid. mp=224.6±1.0°C (lit.^[1] 223–226°C). ¹H NMR (700 MHz, DMSO-*d*₆, δ): 12.01
33 (s, 1H); 7.94 (dd, J=9.3, 4.7 Hz, 1H); 7.74 (dd, J=9.3, 3.0 Hz, 1H); 7.62-7.59 (m, 1H); 7.51 (s,
34 1H); 6.96-6.92 (m, 2H); 6.71 (dd, J=8.9, 4.7 Hz, 2H); 3.71 (s, 3H). ¹⁹F NMR (376 MHz,
35 DMSO-*d*₆, δ): −117.95 (br m, 1F); −125.66 (br m, 1F). IR (KBr) ν=3328, 3237, 3004, 2952,
36 1711, 1565, 1546, 1508, 1484, 1435, 1409, 1358, 1292, 1272, 1226, 1155, 958, 833, 809, 771,
37 739, 698, 564, 529 cm⁻¹. HRMS (ESI) *m/z*: [M + Na]⁺calcd for C₁₇H₁₂F₂N₂O₃Na, 353.0708;
38 found, 353.0701 (+2.1 ppm). Anal. calcd for C₁₇H₁₂F₂N₂O₃: C, 61.82; H, 3.66; N, 8.48;
39 found: C 61.63, H 3.63, N, 8.40.
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

2-Methoxycarbonyl-3-((4-chlorophenyl)amino)-6-chloro-4-quinolone (3c). The synthesis of **3c** was carried out following the procedure reported for **3a** using 3.121 g (7.89 mmol) of **2c** and 40 mL of Dowtherm™ A respectively. The product **3c** (2.530 g, 88.2 %) was isolated as yellow solid. mp=258.4±0.7°C (lit.^[1] 247–248.5°C). ¹H NMR (700 MHz, DMSO-*d*₆, δ): 12.10 (s, 1H); 8.04 (d, J=2.5 Hz, 1H); 7.90 (d, J=9.0 Hz, 1H); 7.72 (dd, J=9.0, 2.5 Hz, 1H); 7.70 (s, 1H); 7.13-7.10 (m, 2H); 6.70-6.67 (m, 2H); 3.75 (s, 3H). ¹³C{¹H} NMR (101 MHz, DMSO-*d*₆, δ): 172.51; 163.42, 144.66; 137.33; 132.30; 128.21; 127.87; 124.96; 124.46; 123.89; 121.94; 121.90; 116.84; 53.14. IR (KBr) ν= 3338, 3226, 2948, 1713, 1565, 1493, 1469, 1438, 1404, 1358, 1296, 1270, 1243, 1217, 1174, 1093, 1071, 977, 946, 842, 822, 773, 760, 710, 663, 540, 520 cm⁻¹. HRMS (ESI) *m/z*: [M + Na]⁺ calcd for C₁₇H₁₂Cl₂N₂O₃Na, 385.0117; found, 385.0105 (+3.2 ppm). Anal. calcd for C₁₇H₁₂Cl₂N₂O₃: C, 56.22; H, 3.33; Cl, 19.52; N, 7.71; found: C 55.82, H 3.36, N, 7.60.

Dibenzo[b,g][1,5]naphthyridine-6,12(5H,11H)-dione (Epi). A mixture of 83.2 g of polyphosphoric acid H_{2+n}P_nO_{3n+1} (115% H₃PO₄ basis) and **3a** (8.320 g, 28.27 mmol) was heated at 150°C for 3.5 h under stirring. The mixture was then cooled to ~50°C and then water (700 mL) was slowly added, keeping the temperature constant until the exothermic process ceased. The reaction mixture was filtered through a sintered glass filter (G4) and the collected solid was washed several times with water (7x150 mL) until free of acid and subsequently with cold methanol (3x150 mL). Eventually, the solid was dried under vacuum at 80°C affording **Epi** (6.59 g, 88.9 %) as a greenish-yellow powder. mp >400°C. ¹H NMR (700 MHz, DMSO-*d*₆, δ): 11.92 (br s, 2H); 8.29 (ddd, J=8.2, 1.5, 0.45 Hz, 2H), 8.09 (ddd, J=8.6, 1.1, 0.65 Hz, 2H), 7.76 (ddd, J=8.6, 6.7, 1.5 Hz, 2H), 7.33 (ddd, J=8.2, 6.7, 1.1 Hz, 2H). IR (KBr) ν= 3216, 3189, 3163, 3126, 2954, 1627, 1583, 1564, 1517, 1469, 1423, 1381, 1370,

1328, 1297, 1245, 1100, 1025, 937, 801, 744, 700, 531 cm⁻¹. Anal. calcd for C₁₆H₁₀N₂O₂: C, 73.27; H, 3.84; N, 10.68; found: C, 73.67; H, 3.87; N, 10.74.

2,8-difluorodibenzo[*b,g*][1,5]naphthyridine-6,12(5*H*,11*H*)-dione (**2F-Epi**). The synthesis of **2F-Epi** was carried out following the procedure reported for **Epi** using 2.146 g (6.50 mmol) of **3b** and 21.5 g of polyphosphoric acid H_{2+n}P_nO_{3n+1} (115% H₃PO₄ basis) respectively. The product **2F-Epi** (1.782 g, 92.0 %) was isolated as yellow solid. mp >400°C. ¹H NMR (700 MHz, D₂SO₄, δ): 8.71-8.65 (m, 2H); 8.50-8.45 (m, 2H); 8.41-8.35 (m, 2H). ¹⁹F NMR (376 MHz, D₂SO₄, δ): -109.20 (br m, 2F). IR (KBr) ν= 3204, 3170, 3096, 2994, 1589, 1571, 1561, 1520, 1481, 1387, 1308, 1242, 1212, 1084, 975, 868, 822, 725, 659, 568, 538 cm⁻¹. Anal. calcd for C₁₆H₈F₂N₂O₂: C, 64.43; H, 2.70; N, 9.39; found: C, 64.23; H, 2.69; N, 9.36.

2,8-dichlorodibenzo[*b,g*][1,5]naphthyridine-6,12(5*H*,11*H*)-dione (**2Cl-Epi**). The synthesis of **2Cl-Epi** was carried out following the procedure reported for **Epi** using 2.340 g (6.44 mmol) of **3c** and 23.4 g of polyphosphoric acid H_{2+n}P_nO_{3n+1} (115% H₃PO₄ basis) respectively. The product **2Cl-Epi** (2.092 g, 98.1 %) was isolated as yellow solid. mp >400°C. ¹H NMR (700 MHz, D₂SO₄, δ): 8.81 (s, 2H); 8.58-8.52 (m, 2H); 8.50-8.44 (m, 2H). IR (KBr) ν= 3208, 3180, 3115, 3076, 3012, 1616, 1581, 1557, 1505, 1462, 1371, 1303, 1233, 1182, 1140, 1114, 1071, 952, 886, 821, 735, 702, 642, 557, 528 cm⁻¹. Anal. calcd for C₁₆H₈Cl₂N₂O₂: C, 58.03; H, 2.43; N, 8.46; found: C, 57.74; H, 2.45; N, 10.65.

*Di-tert-butyl 6,12-dioxodibenzo[*b,g*][1,5]naphthyridine-5,11(6*H*,12*H*)-dicarboxylate (di-tBOC-Epi) and tert-butyl 6,12-dioxo-11,12-dihydrodibenzo[*b,g*][1,5]naphthyridine-5(6*H*)-carboxylate (mono-tBOC-Epi)*. A mixture of epindolidione (**Epi**, 790 mg, 3.01 mmol), 4-dimethylaminopyridine (DMAP, 736 mg, 6.0 mmol) in dry THF (75 mL) was stirred at room

1 temperature. After 15 min, di-*tert*-butyl dicarbonate ((tBOC)₂O, 10.53 g, 48.25 mmol) was
2 added in one portion. The mixture was stirred at 40°C for 96 h and monitored by thin layer
3 chromatography (TLC). The mixture was then filtrated, and the solid recovered (unreacted
4 **Epi**, 216 mg). The filtrate was concentrated in *vacuo* to remove solvent and excess of
5 tBOC₂O at 45°C. The crude residue was purified by flash column chromatography on silica
6 gel using dichloromethane (R_f=0.33) as eluent to afford **di-tBOC-Epi** (488 mg, 35 %) as
7 yellow solid and then dichloromethane/ethyl acetate (92:08=v:v, R_f=0.42) as eluent to afford
8 **mono-tBOC-Epi** (174.5 mg, 16 %) as yellow solid. **di-tBOC-Epi**: ¹H NMR (700 MHz,
9 CDCl₃, δ): 8.45 (dd, J=8.1, 1.6 Hz, 2H); 7.90 (d, J=8.7 Hz, 2H); 7.76 (ddd, J=8.6, 7.0, 1.6 Hz,
10 2H); 7.43-7.40 (m, 2H), 1.69 (s, 18H). ¹³C{¹H} NMR (176 MHz, CDCl₃, δ): 173.27; 150.66;
11 138.40; 134.36 ; 126.94; 123.69, 122.71; 116.17; 86.40; 27.59. IR (KBr) ν= 3007, 2988,
12 2935, 1760, 1630, 1608, 1573, 1478, 1393, 1363, 1347, 1308, 1260, 1238, 1222, 1153,
13 1124, 1108, 1035, 990, 895, 843,781, 745, 695, 572, 557 cm⁻¹. HRMS (ESI) *m/z*: [M +
14 Na]⁺calcd for C₂₆H₂₆N₂O₆Na, 485.1683; found, 485.1680 (+0.9 ppm). Anal. calcd for
15 C₂₆H₂₆N₂O₆: C, 67.52; H, 5.67; N, 6.06; found: C, 67.37; H, 5.64; N, 6.03. **mono-tBOC-Epi**:
16 ¹H NMR (700 MHz, DMSO-*d*₆, δ): 12.20 (br s, 1H); 8.39 (dd, J=8.1, 1.6 Hz, 1H); 8.22 (dd,
17 J=8.1, 1.3 Hz, 1H); 8.09-8.04 (m, 1H); 7.94-7.89 (m, 1H); 7.80 (d, J=8.7 Hz 1H); 7.78-7.74
18 (m, 1H); 7.50-7.45 (m, 1H); 7.38-7.32 (m, 1H); 1.64 (s, 9H). IR (KBr) ν= 3249, 3168, 3010,
19 2977, 2935, 1758, 1618, 1604, 1578, 1490, 1399, 1369, 1335, 1311, 1242, 1222, 1152,
20 1126, 1104, 1024, 1003, 983, 841, 753, 742, 697, 547 cm⁻¹. HRMS (ESI) *m/z*: [M +
21 Na]⁺calcd for C₂₁H₁₈N₂O₄Na, 385.1159; found, 385.1163 (-0.7 ppm). Anal. calcd for
22 C₂₁H₁₈N₂O₄: C, 69.60; H, 5.01; N, 7.73; found: C 69.31, H 5.04, N, 7.62.
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56

57 Crystal Structure Determination

58
59 Single-crystal structure analysis of 2Cl-Epi was carried out on a Bruker Smart APEX
60 diffractometer operating with Mo-K α radiation (λ = 0.71073 Å). The structures were solved by
61
62
63
64
65

direct methods (SHELXS-97) and refined by full-matrix least squares on F² (SHELXL-97).⁶
 The H atoms were calculated geometrically, and a riding model was applied in the refinement process.

For 2F-Epi, data collections were performed at the X-ray diffraction beamline (XRD1) of the Elettra Synchrotron, Trieste (Italy). Complete datasets were collected at 100 K (nitrogen stream supplied through an Oxford Cryostream 700) with a monochromatic wavelength of 0.700 Å through the rotating crystal method. Images were acquired using a Pilatus 2M image plate detector. The crystals of compound 2F-Epi were dipped in N-paratone and mounted on the goniometer head with a nylon loop. The diffraction data were indexed, integrated and scaled using XDS.^[1S] The compound crystallize with a triclinic unit cell. Complete datasets were obtained by merging two data collections obtained from two crystals mounted with different orientations. The unit cell and space group have also been determined at room temperature and no phase change has been detected. The structures were solved by direct methods using SIR2014,^[2S] Fourier analyzed and refined by the full-matrix least-squares based on F² implemented in SHELXL-2014.^[3S] The Coot program was used for modeling.^[4S] Anisotropic thermal motion modeling was then applied to atoms with full occupancy. Hydrogen atoms were included (except for disordered water molecules) at calculated positions with isotropic $U_{\text{factors}} = 1.2 U_{\text{eq}}$.

The 2X-Epi molecules show an inversion center which is located on an inversion center of the triclinic *P*-1 cell. The asymmetric units therefore contains half 2X-Epi molecule only. No disorder and no solvent molecules are present in this crystal form.

	2F-Epi	2Cl-Epi
Moiety Formula	C ₁₆ H ₈ F ₂ N ₂ O ₂	C ₁₆ H ₈ Cl ₂ N ₂ O ₂
Empirical Formula	C ₁₆ H ₈ F ₂ N ₂ O ₂	C ₁₆ H ₈ Cl ₂ N ₂ O ₂
Formula weight (Da)	298.24	331.14
Temperature (K)	100(2)	298(2)
Wavelength (Å)	0.700	0.71073
Crystal system	triclinic	triclinic
Space Group	<i>P</i> -1	<i>P</i> -1
a (Å)	3.690(1)	3.900(3)
b (Å)	5.976(1)	6.260(5)
c (Å)	13.489(2)	13.593(12)
α (°)	101.785(2)	90.947(11)
β (°)	94.892(6)	96.272(10)
γ (°)	92.309(10)	98.599(9)
V (Å ³)	289.61(10)	326.0(5)
Z	1	1

⁶ G. M. Sheldrick, *SHELXS-97, Program for the Solution of Crystal Structures*, Göttingen, Germany, 1997. See also: G. M. Sheldrick, *Acta Crystallographica*, 1990, **A46**, 467-473

ρ (g·cm ⁻³)	1.710	1.687
F(000)	152.0	168
μ (mm ⁻¹)	0.130	0.51
θ min,max (°)	1.5, 27.8	3.0, 24.0
Resolution (Å)	0.75	0.87
Total refl. collctd	7580	1950
Independent refl.	1412	1022
Obs. Refl. [$F_o > 4\sigma(F_o)$]	1324	547
$I/\sigma(I)$ (all data)	21.87	-
$I/\sigma(I)$ (max resltn)	17.67	-
Completeness (all data)	0.99	0.99
Completeness (max resltn)	0.96	-
Rmerge (all data)	0.062	-
Rmerge (max resltn.)	0.066	-
Multiplicity (all data)	5.4	-
Multiplicity (max resltn)	5	-
Data/restraint/parameters	1397/0/101	1022/0/100
Goof	1.045	0.940
R[$I > 2.0\sigma(I)$], wR2 [$I > 2.0\sigma(I)$]	0.0371, 0.1078	0.058, 0.129
R (all data), wR2 (all data)	0.0385, 0.1102	0.1295, 0.1289
CCDC number	1013233	1013474

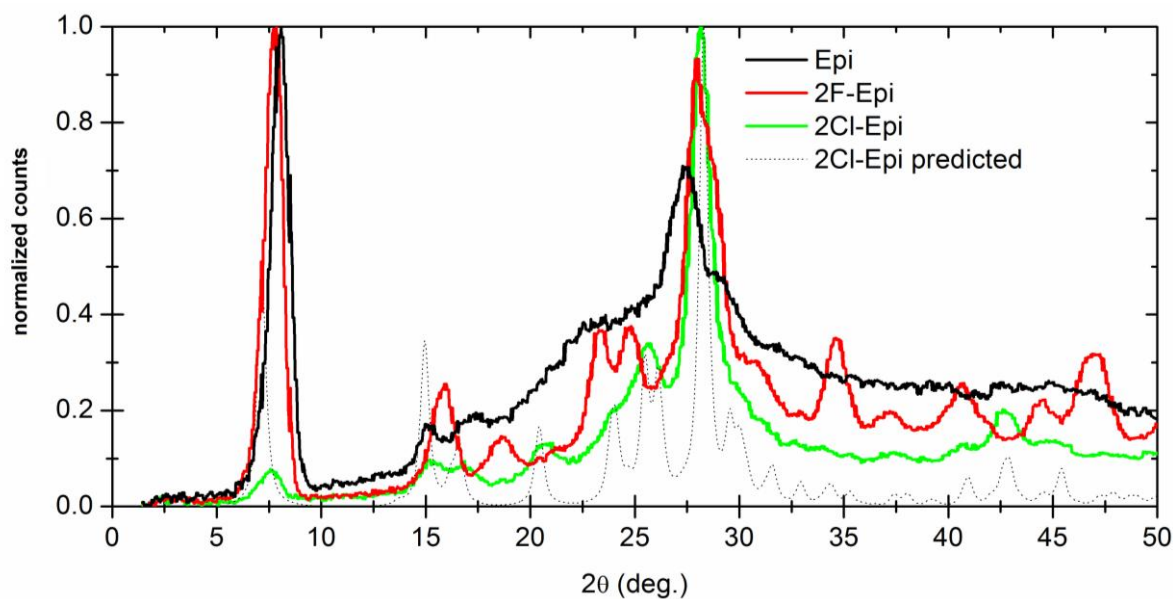


Figure S1. X-ray powder diffraction of the three derivatives, compared with the predicted powder spectrum of 2Cl-Epi calculated based on the X-ray single-crystal structure.

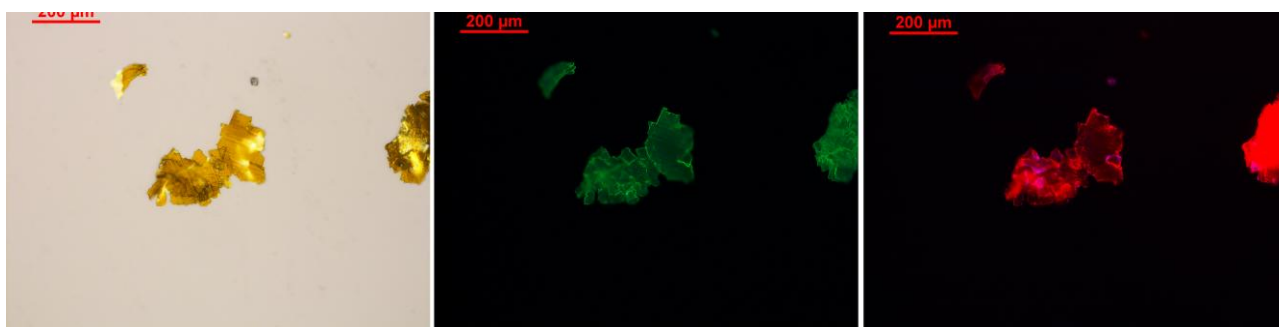


Figure S2. Photomicrographs of epindolidione crystals grown by sublimation. On the left is the episcopic-illuminated bright-field image. The central image is taken using a blue-excitation filter cube, while the right image is taken using a green-excitation filter cube. Both green and red emission can be seen emitting from all parts of the crystals.